



BSI Standards Publication

Welded steel tubes for pressure purposes - Technical delivery conditions

Part 2: Electric welded non-alloy and alloy steel tubes
with specified elevated temperature properties

National foreword

This British Standard is the UK implementation of EN 10217-2:2019. It supersedes BS EN 10217-2:2002+A1:2005, which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee ISE/110, Steel Tubes, and Iron and Steel Fittings.

A list of organizations represented on this committee can be obtained on request to its secretary.

BSI, as a member of CEN, is obliged to publish EN 10217-2:2019 as a British Standard. However, attention is drawn to the fact that during the development of this European Standard, the UK committee voted against its approval.

The UK committee draws users' attention to the fact that BS EN 10217 Parts 1 to 7 are product standards and are therefore intended to assist specifiers, designers and other users of the documents by setting out a series of tube and pipe grades intended for use in pressure applications.

The non-alloy and low-alloy grades in Parts 1 to 6 are comparable (interchangeable) with seamless grades of the same designations in BS EN 10216 Parts 1 to 4. Similarly the stainless grades in Part 7 are comparable to seamless grades of the same designations in

BS EN 10216 Part 5.

It should be noted that guidance on material suitability for specific applications is not provided in product standards. It is therefore important that specifiers, designers and other users of the documents understand the differences between the types and characteristics of the welded pressure pipes covered in the standards so that the appropriate type and grade can be specified or selected for the application concerned.

In particular, it should be noted that, although BS EN 13480 supports essential requirements of EU Directive 2014/68/EU (the Pressure Equipment Directive or PED), the TR1 grades in BS EN 10217-1 are not suitable for use under the PED (as indicated in Table 4 of the Standard). This is because, in particular, they do not meet the essential requirements of the Directive in respect of ageing (determined by the chemical composition) or ductility (specified as minimum Charpy impact requirements). In addition, most HFW TR1 grades imported into the UK are cold-formed and hence the weld seam will not have been heat-treated which means that the weld area is likely to be highly stressed, which can lead to cracking if the tube is subjected to additional processing. The UK committee therefore recommends that users do not use any HFW products certified or sold as being of BS EN 10217-1 TR1 grade. Instead, to ensure PED compliance, the UK committee recommends that hot-

finished HFW tubes in accordance with BS EN 10217-2 should be used for most pressure applications, although BS EN 10217-1 TR2 grades may be considered in some cases. As BS EN 10217-1 TR2 grades and pipes can be used for a whole range of

applications from building services to critical requirements involving gas or chemicals, it is important that the specifier, designer or user selects the most suitable tube or pipe type and grade from the seven parts of the standard provided.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2019
Published by BSI Standards Limited 2019

ISBN 9780580686467

ICS 77.140.75;23.040.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 May 2019.

Amendments/corrigenda issued since publication

Date

Text affected

EUROPEAN STANDARD
NORME EUROPEENNE
EUROPÄISCHE NORM

EN 10217-2

April 2019

ICS 23.040.10;77.140.75

Supersedes EN 10217-2:2002

English Version

Welded steel tubes for pressure purposes -Technical delivery conditions -Part 2:Electric welded non-alloy and alloy steel tubes with specified elevated temperature properties

Tubes soudés en acier pour service sous pression-Conditions techniques de livraison-Partie 2:Tubes soudés électriquement en acier non allié et allié avec caractéristiques spécifiées à température élevée

Geschweißte Stahlrohre für Druckbeanspruchungen-Technische Lieferbedingungen-Teil 2:Elektrisch geschweißte Rohre aus unlegierten und legierten Stählen mit festgelegten Eigenschaften bei erhöhten Temperaturen

This European Standard was approved by CEN on 25 February 2019.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPAISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

©2019 CEN All rights of exploitation in any form and by any means reserved worldwide for CEN national Members.

Ref.No. EN 10217-2:2019 E

Contents

Page

European foreword	4
1 Scope	5
2 Normative references	5
3 Terms and definitions	6
4 Symbols	7
5 Classification and designation	7
5.1 Classification	7
5.2 Designation	7
6 Information to be supplied by the purchaser	7
6.1 Mandatory information	7
6.2 Options	8
6.3 Example of an order	9
7 Manufacturing process	9
7.1 Steelmaking process	9
7.2 Tube manufacture and delivery conditions	9
7.3 Non Destructive Testing Personnel Requirements	10
8 Requirements	10
8.1 Genera	10
8.2 Chemical composition	10
8.2.1 Cast analysis	10
8.2.2 Product analysis	12
8.3 Mechanical properties	12
8.4 Appearance and internal soundness	13
8.4.1 Weld seam	13
8.4.2 Tube surface	14
8.4.3 Internal soundness	14
8.5 Straightness	14
8.6 Preparation of ends	14
8.7 Dimensions, masses and tolerances	15
8.7.1 Diameter and wall thickness	15
8.7.2 Mass	19
8.7.3 Lengths	19
8.7.4 Tolerances	19
9 Inspection	20
9.1 Type of inspection	20
9.2 Inspection documents	20
9.2.1 Types of inspection documents	20
9.2.2 Content of inspection documents	21
9.3 Summary of inspection and testing	21
10 Sampling	23
10.1 Frequency of tests	23
10.1.1 Test unit	23
10.1.2 Number of sample tubes per test unit	23
10.2 Preparation of samples and test pieces	24
10.2.1 Selection and preparation of samples for product analysis	24
10.2.2 Location, orientation and preparation of samples and test pieces for mechanical tests	24
11 Verification of test methods	25

11.1	Chemical analysis	25
11.2	Tensile test on the tube body	25
11.2.1	At room temperature	25
11.2.2	At elevated temperature.....	25
11.3	Transverse tensile test on the weld.....	26
11.4	Flattening test	26
11.5	Ring tensile test	26
11.6	Drift expanding test	26
11.7	Ring expanding test	27
11.8	Impact test	27
11.9	Leak tightness test	28
11.9.1	Hydrostatic test	28
11.9.2	Electromagnetic test	28
11.10	Dimensional inspection	28
11.11	Visual examination	29
11.12	Non-Destructive Testing	29
11.13	Material identification	29
11.14	Retests, sorting and reprocessing	29
12	Marking	30
12.1	Marking to be applied.....	30
12.2	Additional marking	30
13	Protection	30
	Annex A (informative) Technical changes from the previous edition	31
A.1	Introduction	31
A.2	Technical changes	31
	Annex ZA (informative) Relationship between this European Standard and the Essential Requirements of 2014/68/EU.....	33
	Bibliography.....	34

European foreword

This document (EN 10217-2:2019) has been prepared by Technical Committee CEN/TC 459 "ECISS-European Committee for Iron and Steel Standardization"¹, the secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2019, and conflicting national standards shall be withdrawn at the latest by October 2019.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 10217-2:2002.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association, and supports the essential requirements of EU Directive 2014/68/EU.

For relationship with EU Directive 2014/68/EU (formerly 97/23/EC), see informative Annex ZA, which is an integral part of this document.

This European Standard consists of the following parts, under the general title *Welded steel tubes for pressure purposes—Technical delivery conditions*:

—Part 1: *Electric welded and submerged arc welded non-alloy steel tubes with specified room temperature properties*

—Part 2: *Electric welded non-alloy and alloy steel tubes with specified elevated temperature properties*

Part 3: *Electric welded and submerged arc welded alloy fine grain steel tubes with specified room, elevated and low temperature properties*

Part 4: *Electric welded non-alloy steel tubes with specified low temperature properties*

—Part 5: *Submerged arc welded non-alloy and alloy steel tubes with specified elevated temperature properties*

—Part 6: *Submerged arc welded non-alloy steel tubes with specified low temperature properties*

—Part 7: *Stainless steel tubes*

Another European Standard series covering tubes for pressure purposes is:

EN 10216, Seamless steel tubes for pressure purposes.

According to the CEN-CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

¹ Through its subcommittee SC 10 "Steel tubes, and iron and steel fittings" (secretariat: UNI)

1 Scope

This document specifies the technical delivery conditions for two test categories of electric welded tubes of circular cross section, with specified elevated temperature properties, made from non-alloy quality steel or alloy special steel.

NOTE 1 These tube grades are intended to support the essential requirements of EU Directive 2014/68/EU in respect of pressure equipment with specified elevated temperature properties, covered under all relevant Categories as set out in Article 13 of that Directive.

NOTE 2 Once this standard is published in the Official Journal of the European Union (OJEU), presumption of conformity to the Essential Safety Requirements (ESR) of Directive 2014/68/EU is limited to the technical data for the materials in this standard and does not presume adequacy of the material for a specific item of pressure equipment. Consequently, the assessment of the technical data stated in this material standard against the design requirements of a specific item of equipment to verify that the ESRs of the Pressure Equipment Directive are satisfied, needs to be done by the designer or manufacturer of the pressure equipment, taking also into account any subsequent processing procedures which may affect properties of the base materials.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 10020, Definition and classification of grades of steel

EN 10021:2006, General technical delivery conditions for steel products

EN 10027-1, Designation systems for steels — Part 1: Steel names

EN 10027-2, Designation systems for steels — Part 2: Numerical system

EN 10168:2004, Steel products — Inspection documents — List of information and description

EN 10204:2004, Metallic products — Types of inspection documents

EN 10220, Seamless and welded steel tubes — Dimensions and masses per unit length

CEN/TR 10261, Iron and steel — European standards for the determination of chemical composition

EN 10266, Steel tubes, fittings and structural hollow sections — Symbols and definitions of terms for use in product standards

EN ISO 148-1:2016, Metallic materials — Charpy pendulum impact test — Part 1: Test method (ISO 148-1:2016)

EN ISO 377:2017, Steel and steel products — Location and preparation of samples and test pieces for mechanical testing (ISO 377:2017)

EN ISO 2566-1:1999, Steel — Conversion of elongation values — Part 1: Carbon and low alloy steels (ISO 2566-1:1984)

EN ISO 4885, Ferrous materials — Heat treatments — Vocabulary (ISO 4885)

EN ISO 6892-1:2016, Metallic materials — Tensile testing — Part 1: Method of test at room temperature (ISO 6892-1:2016)

EN ISO 6892-2:2018, Metallic materials — Tensile testing — Part 2: Method of test at elevated temperature (ISO 6892-2:2018)

EN ISO 8492:2013, *Metallic materials — Tube — Flattening test (ISO 8492:2013)*

EN ISO 8493:2004, *Metallic materials — Tube — Drift-expanding test (ISO 8493:1998)*

EN ISO 8495:2013, *Metallic materials — Tube — Ring-expanding test (ISO 8495:2013)*

EN ISO 8496:2013, *Metallic materials — Tube — Ring tensile test (ISO 8496:2013)*

EN ISO 10893-1:2011, *Non-destructive testing of steel tubes — Part 1: Automated electromagnetic testing of seamless and welded (except submerged arc-welded) steel tubes for the verification of hydraulic leak tightness (ISO 10893-1:2011)*

EN ISO 10893-2:2011, *Non-destructive testing of steel tubes — Part 2: Automated eddy current testing of seamless and welded (except submerged arc-welded) steel tubes for the detection of imperfections (ISO 10893-2:2011)*

EN ISO 10893-3:2011, *Non-destructive testing of steel tubes — Part 3: Automated full peripheral flux leakage testing of seamless and welded (except submerged arc-welded) ferromagnetic steel tubes for the detection of longitudinal and/or transverse imperfections (ISO 10893-3:2011)*

EN ISO 10893-8:2011, *Non-destructive testing of steel tubes — Part 8: Automated ultrasonic testing of seamless and welded steel tubes for the detection of laminar imperfections (ISO 10893-8:2011)*

EN ISO 10893-10:2011, *Non-destructive testing of steel tubes — Part 10: Automated full peripheral ultrasonic testing of seamless and welded (except submerged arc-welded) steel tubes for the detection of longitudinal and/or transverse imperfections (ISO 10893-10:2011)*

EN ISO 10893-11:2011, *Non-destructive testing of steel tubes — Part 11: Automated ultrasonic testing of the weld seam of welded steel tubes for the detection of longitudinal and/or transverse imperfections (ISO 10893-11:2011)*

EN ISO 14284, *Steel and iron — Sampling and preparation of samples for the determination of chemical composition (ISO 14284)*

ISO 11484:2009, *Steel products — Employer's qualification system for non-destructive testing (NDT) personnel*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN 10020, EN 10021, EN 10266, EN ISO 4885 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

— IEC Electropedia: available at <http://www.electropedia.org/>

— ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1

test category

classification that indicates the extent and level of inspection and testing

3.2

employer

organisation for which a person works on a regular basis

Note 1 to entry: The employer may be either the tube manufacturer or a third party organization providing services, such as Non-Destructive Testing (NDT).

3.3

EW

electric welded tube

tubular product having one longitudinal seam weld produced by electric (resistance) welding where the strip edges to be welded are mechanically pressed together and the heat for the welding process is generated by the resistance to flow of low or high frequency electric current applied by either a conduction or induction process

3.4

HFW

high frequency welded tube

EW tube produced specifically using a welding current frequency equal to or greater than 100 kHz

4 Symbols

For the purposes of this document, the symbols given in EN 10266 apply.

5 Classification and designation

5.1 Classification

In accordance with the classification system in EN 10020, the steel grades P195GH, P235GH and P265GH in this standard are classified as non-alloy quality steels and the steel grade 16Mo3 is classified as an alloy special steel

5.2 Designation

5.2.1 For the tubes covered by this document, the steel designation consists of:

—the number of this European Standard, e.g. EN 10217-2;

plus either:

—the steel name in accordance with EN 10027-1;

or:

—the steel number allocated in accordance with EN 10027-2.

5.2.2 The steel name of non-alloy steel grades is designated by:

—the capital letter P for pressure purposes;

—the indication of the specified minimum yield strength at room temperature for thickness T less than or equal to 16 mm, expressed in MPa (see Table 4);

—the symbols GH for elevated temperature.

5.2.3 The steel name of alloy steel grade 16Mo3 is designated by the chemical composition (see Table 2).

6 Information to be supplied by the purchaser

6.1 Mandatory information

The following information shall be supplied by the purchaser at the time of enquiry and order:

a) the quantity (mass, total length or number of tubes of set length);

b) the term 'tube' and tube type, HFW;

- c) the dimensions (outside diameter D and wall thickness T) (see Table 6);
- d) the random length range (see 8.7.3).
- e) for tubes with a $D/T > 100$, out of roundness limits (see 8.7.4.4).
- f) the designation of the steel grade in accordance with this document (see 5.2);
- g) the test category for non-alloy steel (see 9.3).

6.2 Options

A number of options are specified in this document and these are listed below. In the event that the purchaser does not indicate a wish to implement any of these options at the time of enquiry and order, the tubes shall be supplied in accordance with the basic specification (see 6.1).

- 1) Tube manufacturing route (see 7.2.1);
- 2) Restriction on copper and tin content (see Table 2);
- 3) Product analysis (see 8.2.2);
- 4) Verification of tube body impact energy (see 8.3);
- 5) Additional longitudinal impact test at -10°C for non-alloy steel grades (see Table 4);
- 6) Verification of proof strength $R_{p0.2}$ at elevated temperature (see 8.3);
- 7) Selection of method for verification of leak-tightness test (see 8.4.3.1);
- 8) Non-Destructive Testing of test category 2 tubes for the detection of transverse imperfections (see 8.4.3.2);
- 9) Non-Destructive Testing of test category 2 tubes for the detection of laminar imperfections (see 8.4.3.2);
- 10) Special end preparation (see 8.6);
- 11) Exact lengths (see 8.7.3);
- 12) Inspection document 3.2 in place of the standard 3.1 inspection certificate (see 9.2.1);
- 13) Verification of tensile strength of the weld in the transverse direction for tubes of outside diameter $D > 219,1$ mm (see Table 10);
- 14) Agreement of a different test pressure for hydrostatic leak-tightness test (see 11.9.1);
- 15) Wall thickness measurement away from the ends (see 11.10);
- 16) Selection of the Non-Destructive Testing method for the inspection of the weld seam of test category 1 tubes (see 11.12.1);
- 17) Selection of the Non-Destructive Testing method for the full peripheral inspection of test category 2 tubes (see 11.12.2);
- 18) Additional marking (see 12.2);
- 19) Protection (see Clause 13).

6.3 Example of an order

500m of HFW tube with an outside diameter of 168,3 mm, a wall thickness of 4,5 mm in accordance with EN 10217-2, made of steel grade P265GH, test category 1, in 6m random lengths, with a 3.2 inspection certificate in accordance with EN 10204:

500m-HFW Tube-168,3×4,5-EN 10217-2—P265GH-TC1-6m-Option 12:3.2

7 Manufacturing process

7.1 Steelmaking process

The steelmaking process is at the discretion of the steel or tube manufacturer with the exception that steel produced by the open hearth (Siemens-Martin) process shall not be employed unless in combination with a secondary steelmaking or ladle refining process.

Steels shall be fully killed and contain nitrogen binding elements, details of which shall be reported.

NOTE This excludes the use of rimming, balanced or semi-killed steel.

7.2 Tube manufacture and delivery conditions

7.2.1 The tubes shall be manufactured by an electric welding process employing high frequency welding (HFW), of minimum frequency 100 kHz in accordance with one of the manufacturing routes specified in Table 1.

Unless Option 1 is specified the manufacturing route is at the discretion of the manufacturer.

Option 1: The manufacturing route from Table 1 is specified by the purchaser.

The finished tubes shall not include the welds used to join together the lengths of strip prior to forming.

7.2.2 Tube production welding shall be carried out by qualified personnel in accordance with documented procedures. For tubes to be used in pressure equipment under European legislation, manufacturers shall employ an established procedure for the approval of welding operatives.

The production (welding) process shall be qualified and approved under the tube manufacturer's own QA system. Only HFW tubes (see 3.4) shall be supplied for pressure equipment under European legislation.

7.2.3 The delivery conditions of tubes covered by this document are shown in Table 1.

Table 1—Tube manufacturing route and delivery condition

Route N (according to Part 1)	Manufacturing Starting material	Forming operation	Acceptable delivery condition a
1c	As(hot)rolled strip	Cold formed and welded	NP
1d			NR
2b	Normalized rolled strip		NW
2c			NP
2d			NR
a NP=tube full body normalized;NW=normalized weld zone;NR=normalized rolled or hot (stretch)reduced within the normalizing temperature range.			

7.3 Non Destructive Testing Personnel Requirements

7.3.1 All NDT activities shall be carried out by qualified and competent level 1,2 and/or 3 personnel, authorized to carry out this work by the employer.

7.3.2 The qualification for levels 1 and 2 personnel shall be in accordance with ISO 11484 or, at least, an equivalent to it.

7.3.3 It is recommended for the level 3 personnel to be suitably certified, either in accordance with EN ISO 9712 or, at least, an equivalent to it.

7.3.4 The operating authorization issued by the employer shall be in accordance with a written procedure.

7.3.5 All NDT operations shall be authorised by a level 3 NDT technician approved by the employer.

NOTE The definition of levels 1,2 and 3 can be found in appropriate standards, e.g. EN ISO 9712 and ISO 11484.

8 Requirements

8.1 General

The tubes shall conform to the requirements of this document when supplied in a delivery condition in accordance with Table 1 and inspected in accordance with the specified requirements in Table 10.

Tubes shall be suitable for hot and cold bending.

In addition, the general technical delivery requirements specified in EN 10021 shall apply.

8.2 Chemical composition

8.2.1 Cast analysis

The cast analysis reported by the steel producer shall apply and shall conform to the requirements of Table 2.

When welding tubes produced in accordance with this document, account should be taken of the fact that the behaviour of the steel during and after welding is dependent not only on the steel analysis, but also on the welding process, including heat input, any applied heat treatment and the conditions of preparing for and carrying out the welding.

Table 2—Chemical composition (cast analysis)a in % by mass

Steel grade	Steel name	Steel number	C	Si	Mn	P	S	Cr	Mo	Ni	Al tot	Cu b max.	Nb d max.	Ti d max.	vd max.	Cr+Cu+Mo+Ni max.
P195GH		1. 0348	≤0, 13	0, 35	≤0, 70	0, 025	0, 020	0, 30	≤0, 08	0, 30	≥0, 020C	0, 30	0, 010	0, 03	0, 02	0, 70
P235GH		1. 0345	≤0, 16	0, 35	≤1, 20	0, 025	0, 020	0, 30	≤0, 08	0, 30	≥0, 020C	0, 30	0, 010	0, 03	0, 02	0, 70
P265GH		1. 0425	≤0, 20	0, 40	≤1, 40	0, 025	0, 020	0, 30	≤0, 08	0, 30	≥0, 020C	0, 30	0, 010	0, 03	0, 02	0, 70
16Mo3		1. 5415	0, 12 to 0, 20	0, 35	0, 40 to 0, 90	0, 025	0, 020	0, 30	0, 25 to 0, 35	0, 30	≤0, 040	0, 30				

a Elements no quoted in this Table shall not be intentionally added to the steel without the agreement of the purchaser, except for elements which may be added for finishing the cast. All appropriate measures shall be taken to prevent the addition of undesirable elements from scrap or other materials used in the steel making process which would have a negative impact on the mechanical properties, ageing and the suitability of the material.

b **Option 2:** In order to facilitate subsequent forming operations an agreed maximum copper content lower than indicated and an agreed specified maximum tin content shall apply;

c For A/N ratios ≥ 2, the nitrogen is fixed by niobium, titanium or vanadium, details of which shall be reported, this requirement does not apply except that when using titanium, the steel producer shall verify that $(Al+Ti)/2 \geq 0,020\%$;

d The content of these elements need not to be reported unless intentionally added to the cast.

8.2.2 Product analysis

Unless Option 3 is specified, only the cast analysis shall be reported.

Option 3: A product analysis for the tubes shall be supplied.

Table 3 specifies the permissible deviations of the product analysis from the specified limits on cast analysis given in Table 2.

Table 3—Permissible deviations of the product analysis from specified limits on cast analysis given in Table 2

Element	Limiting value for the cast Analysis in accordance with Table 2 %by mass	Permissible deviation of the product analysis %by mass
C	$\leq 0,20$	+0,02
Si	$\leq 0,40$	+0,05
Mn	$\leq 1,00$	+0,05
	$>1,00$ to $\leq 1,40$	$\pm 0,10$
P	$\leq 0,025$	+0,005
S	$\leq 0,020$	+0,005
Cr	$\leq 0,30$	+0,05
Mo	$\leq 0,35$	+0,03
Ni	$\leq 0,30$	+0,05
Al	$\leq 0,040$	+0,005
Cu	$\leq 0,30$	+0,05
Nb	$\leq 0,010$	+0,005
Ti	$\leq 0,030$	+0,010
V	$\leq 0,02$	+0,01
Cr+Cu+Mo+Ni	$\leq 0,70$	+0,05

8.3 Mechanical properties

The mechanical properties of the tubes, in a specified delivery condition from Table 1, shall conform to the requirements of Table 4 and the relevant additional tests specified in 11.3 to 11.7, irrespective of whether the test results are actually verified or not (see Table 10 for a summary of the inspection and verification testing required).

Unless Option 4 is specified, the impact properties need not be verified.

Option 4: The tube body impact properties shall be verified (see 10.2.2.5 and 11.8).

Table 4—Mechanical properties for wall thickness $T \leq 16$ mm

Steel grade		Tensile properties at room temperature				Impact properties b				
Steel name	Steel number	Upper yield strength or proof strength R_{eH} or $R_{p0.2}$ min MPa	Tensile strength R_m MPa	Elongation at A min. %		Minimum average absorbed energy $KV_2 dJ$ at a temperature of °C				
						l			t	
					t	20	0	-10	20	0
P195GH	1. 0348	195	320–440	27	25		40	28e		27
P235GH	1. 0345	235	360–500	25	23		40	28e		27
P265GH	1. 0425	265	410–570	23	21		40	28e		27
16Mo3	1. 5415	280	450–600	22	20	40			27	
See 11.2.1 To be verified only when Options 4 and/or 5 are specified l=longitudinal t=transverse d KV_2 =impact values obtained using a 2 mm radius striker in accordance with EN ISO148-1 Option 5: In addition to the specified impact test at 0°C, an additional longitudinal impact test shall be performed at -10°C.										

The minimum proof strength $R_{p0.2}$ values of the tube grades at elevated temperature are given in Table 5. These need not be verified, unless Option 6 is specified.

Option 6: Proof strength $R_{p0.2}$ at elevated temperatures shall be verified. The test temperature from Table 5 shall be agreed at the time of enquiry and order.

The manufacturer shall have data available to demonstrate that their products are capable of achieving the minimum elevated temperature properties shown.

Table 5—Minimum 0,2% proof strength ($R_{p0.2}$) at elevated temperature for wall thickness $T \leq 16$ mm

Steel grade		$R_{p0.2}$ min. MPa at a temperature of °C						
Steel name	Steel number	100	150	200	250	300	350	400
P195GH	1. 0348	175	165	150	130	113	102	94
P235GH	1. 0345	198	187	170	150	132	120	112
P265GH	1. 0425	226	213	192	171	154	141	134
16Mo3	1. 5415	243	237	224	205	173	159	156

8.4 Appearance and internal soundness

8.4.1 Weld seam

The weld area shall be free from cracks and lack of fusion. Repairs to the weld seam of HFW tubes are not permitted.

NOTE For strip alignment (radial offset) and tolerances in the weld region, see 8.7.4.2.

8.4.2 Tube surface

8.4.2.1 The tubes shall be free from external and internal surface defects that can be detected by visual examination of the surfaces that are accessible without the use of special equipment.

8.4.2.2 The internal and external surface finish of the tubes shall be typical of the manufacturing process and, where applicable, the heat treatment employed. Normally the finish and surface condition shall be such that any surface imperfections requiring dressing can be identified.

8.4.2.3 It shall be permissible to dress, only by grinding or machining, surface imperfections provided that after doing so, the wall thickness in the dressed area is not less than the specified minimum wall thickness. All dressed areas shall blend smoothly into the contour of the tube.

8.4.2.4 Any surface imperfection, which is demonstrated to be deeper than 5% of the wall thickness or 3 mm, whichever is the smaller, shall be dressed.

8.4.2.5 Surface imperfections which extend below the specified minimum wall thickness shall be considered defects and tubes containing these shall be deemed not to conform with this document and shall be rejected.

8.4.3 Internal soundness

8.4.3.1 Leak-tightness

The tubes shall be assessed for leak tightness by either a hydrostatic test (see 11.9.1) or an electromagnetic test (see 11.9.2).

Unless Option 7 is specified, the choice of the test method is at the discretion of the manufacturer.

Option 7: The test method for verification of leak-tightness in accordance with 11.9.1 or 11.9.2 is specified by the purchaser.

8.4.3.2 Non-Destructive Testing

The full length of the weld seam of tubes of test category 1 shall be subjected to Non-Destructive Testing for the detection of imperfections in accordance with 11.12.1.

The full length of the weld seam and the body of tubes of test category 2 shall be subjected to Non-Destructive Testing for the detection of longitudinal imperfections, in accordance with 11.12.2.

For test category 2 tubes, if Options 8 or 9 are specified, the following additional NDT testing shall also be applied.

Option 8: The tubes of test category 2 shall be subjected to Non-Destructive Testing for the detection of transverse imperfections in accordance with 11.12.3.

Option 9: The tubes of test category 2 shall be subjected to Non-Destructive Testing for the detection of laminar imperfections in accordance with 11.12.4.


8.5 Straightness

The deviation from straightness of any tube length L shall not exceed $0,0015 L$. Deviations from straightness over any one metre length shall not exceed 3 mm.

8.6 Preparation of ends

Unless Option 10 is specified, tubes shall be delivered with square cut ends free from excessive burrs.

Option 10: The tubes shall be delivered with bevelled ends (see Figure 1). The bevel shall have an angle α of $30^\circ \begin{smallmatrix} +5^\circ \\ 0^\circ \end{smallmatrix}$ with a root face C of $1,6\text{mm} \pm 0,8 \text{ mm}$. Beveling is applicable for specified wall thicknesses $\geq 3,2 \text{ mm}$, except that for wall thickness $T \geq 20 \text{ mm}$, an agreed alternative bevel may be specified.

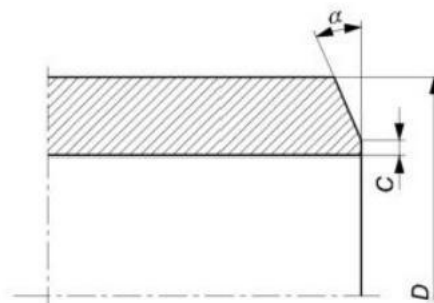

Key

D outside diameter
 α bevel angle
C root face of bevelled end

Figure 1—Tube end bevel

8.7 Dimensions, masses and tolerances

8.7.1 Diameter and wall thickness

Tubes shall be delivered by outside diameter D and wall thickness T .

The preferred outside diameters D and wall thicknesses T have mainly been selected from EN 10220 and are given in Table 6.

NOTE Dimensions other than those in Table 6 may be agreed.

Table 6—Preferred dimensions

Outside diameter D Series a			Wall thicknesses, T																			Dimensions in millimetres			
1	2	3	1, 4	1, 6	1, 8	2	2, 3	2, 6	2, 9	3, 2	3, 6	4	4, 5	5	5, 6	6, 3	7, 1	8	8, 8	10	11	12, 5	14, 2	16	
10, 2																									
	12																								
	12, 7																								
13, 5																									
		14																							
	16																								
17, 2																									
		18																							
	19																								
	20																								
21, 3																									
		22																							
	25																								
		25, 4																							
26, 9																									
		30																							
	31, 8																								
	32																								
33, 7																									
		35																							
	38																								
	40																								

Outsidediameter D Series a			Wall thicknesses, T																						
1	2	3	1,4	1,6	1,8	2	2,3	2,6	2,9	3,2	3,6	4	4,5	5	5,6	6,3	7,1	8	8,8	10	11	12,5	14,2	16	
42,4																									
		44,5																							
48,3																									
	51																								
		54																							
	57																								
60,3																									
	63,5																								
	70																								
		73																							
76,1																									
		82,5																							
88,9																									
	101,6																								
		108																							
114,3																									
	127																								
	133																								
139,7																									
		141,3																							
		152,4																							
		159																							
	165,1																								
168.3																									
		177,8																							

Outside diameter D Series a			Wall thicknesses, T																						
1	2	3	1, 4	1, 6	1, 8	2	2, 3	2, 6	2, 9	3, 2	3, 6	4	4, 5	5	5, 6	6, 3	7, 1	8	8, 8	10	11	12, 5	14, 2	16	
		193, 7																							
219, 1																									
		244. 5																							
273																									
323, 9																									
355, 6																									
406, 4																									
457																									
508																									
610																									
series 1	series 2	series 3=diameters for special applications	diameters =	for	for which diameters	all	the	accessories for which	accessories needed	not	for	the	all	the	construction	of	piping	systems	are	standardised	are	standardised			

8.7.2 Mass

For the mass per unit length the provisions of EN 10220 apply.

8.7.3 Lengths

Unless Option 11 is specified, the tubes shall be delivered in random lengths. The delivery range shall be agreed at the time of enquiry and order.

Option 11: The tubes shall be delivered in exact lengths, the length to be specified at the time of enquiry and order. For tolerances on exact lengths see 8.7.4.3.

8.7.4 Tolerances

8.7.4.1 Tolerances on diameter and thickness

The diameter and the wall thickness of the tubes shall be within the tolerance limits given in Table 7.

Table 7—Tolerances on outside diameter and wall thickness

Dimensions in millimetres

Outside diameter D	Tolerance on outside diameter	Tolerance on wall thickness a	
		$T \leq 5$	$5 < T \leq 16$
$\leq 219,1$	$\pm 1\%$ or $\pm 0,5$ whichever is the greater	$\pm 10\%$ or $\pm 0,3$ whichever is the greater	$\pm 8\%$
$> 219,1$	$\pm 0,75 \%$		

a The plus tolerance excludes the weld area (see 8.7.4.2).

8.7.4.2 Height of the weld seam


The height of the external and internal weld beads shall be within the limits indicated in Table 8.

Table 8—Maximum height of the weld bead

Dimensions in millimetres

Outside	Inside
Trimmed Flush	Trimmed or $0,5 + 0,05 T$

The radial offset of the strip edges after trimming, see Figure 2, shall not cause the remaining wall thickness to be less than the minimum set out in Table 7.



Key

1 remaining wall thickness at the weld

Figure 2—Radial offset of the strip edges (HFW tube)

8.7.4.3 Tolerances on exact length

The tolerances for exact lengths shall be as given in Table 9.

Table 9—Tolerances on exact length

Dimensions in millimetres

Length range L	Tolerance for outside diameter (D)	
	<406,4	≥406,4
$L \leq 6000$	$\begin{smallmatrix} +10 \\ 0 \end{smallmatrix}$	$\begin{smallmatrix} +25 \\ 0 \end{smallmatrix}$
$6000 < L \leq 12000$	$\begin{smallmatrix} +15 \\ 0 \end{smallmatrix}$	$\begin{smallmatrix} +50 \\ 0 \end{smallmatrix}$
$L > 12000$	$\begin{smallmatrix} +\text{by agreement} \\ 0 \end{smallmatrix}$	

8.7.4.4 out-of-roundness

The out-of-roundness O shall be calculated using the following Formula(1):

$$O = \frac{D_{\max} - D_{\min}}{D} \times 100 \quad (1)$$

where

O is the out-of-roundness in %;

D is the specified outside diameter in mm;

D_{max}, D_{min} is the maximum and minimum outside diameter measured in the same plane in mm.

For tubes of D ≤ 406,4 mm, out-of-roundness shall be included in the limits of the diameter tolerances.

For tubes of D > 406,4 mm and with D/T ≤ 100, out-of-roundness shall not exceed 2%.

For tubes with a D/T ratio > 100 the values for out-of-roundness shall be agreed at the time of enquiry and order.

9 Inspection

9.1 Type of inspection

Conformity to the requirements of the order, for tubes in accordance with this document, shall be verified by specific inspection.

9.2 Inspection documents

9.2.1 Types of inspection documents

Unless Option 12 is specified an inspection certificate 3.1 in accordance with EN 10204 shall be issued. The tube manufacturer shall confirm in this whether they are operating according to a “quality assurance system”, certified by a competent body established within the community, and have undergone a specific assessment for materials and processes relevant to the manufacture of welded tubes (see 7.2.2 and NOTE below).

Option 12: An inspection certificate 3.2 in accordance with EN 10204 shall be issued.

When an inspection certificate 3.2 is specified, this shall be prepared by the manufacturer's authorized representative(s). The purchaser shall notify the manufacturer of the name and address of the organization or person that will carry out the inspection and confirm who will validate and issue the inspection document.

9.2.2 Content of inspection documents

9.2.2.1 The content of the inspection document shall be in accordance with EN 10168 as shown in 9.2.2.2. The inspection documents shall include a statement confirming the conformity of the products to the requirements of this specification and to the order.

9.2.2.2 The inspection certificate shall contain the following codes and information:

A	commercial transactions and parties involved;
B	description of products to which the inspection document applies;
C01-C03	location of the samples, direction of the test pieces and testing temperature;
C10-C13	tensile test(s);
C40-C43	impact test results if verified;
C50-C69	other mechanical tests (e.g. flattening, ring tensile, drift or ring expanding);
C71-C92	cast analysis reported by the steel producer and product analysis, if applicable;
D01	statement that marking and identification, surface appearance, shape and dimensional properties are satisfactory;
D02-D99	statement confirming that leak tightness test and applicable NDT testing has been carried out, and the test results are satisfactory;
Z	validation.

—Reference to specific assessment under pressure equipment European legislation for materials and processes relevant to manufacture of welded tubes;

—Reference to welding process approval, where applicable;

—Reference to non-destructive testing operators approval, where applicable;

—In addition, where applicable, the manufacturer shall make reference to any certification of his “quality assurance system” by a competent body established within the community, see 9.2.1.

9.3 Summary of inspection and testing

Inspection and testing shall be carried out as stated in Table 10.

Non-alloy steel tubes shall be inspected and tested in accordance with test category 1 or test category 2 as specified at the time of enquiry and order (see 6.1).

Tubes of steel grade 16Mo3 shall be inspected and tested in accordance with test category 2.

Table 10—Summary of inspection and verification testing

Type of inspection and test		Frequency of testing	Refer to	Test category	
				1	2
Mandatory Tests	Cast analysis (reported by steel producer)	One per cast	8.2.1 and 11.1	X	X
	Tensile test on tube body at room temperature	One test per sample tube	8.3, 10.2.2.2 and 11.2.1	X	X
	Flattening test for $D < 600$ mm and T/D ratio $\leq 0,15$ but $T \leq 40$ mm or Ring tensile test for $D > 150$ mm and $T \leq 40$ mm	Two tests per sample tube a or One test per sample tube	8.3, 10.2.2.4 11.4 and 11.5	X	X
	Drift expanding test for $D \leq 150$ mm and $T \leq 10$ mm or b Ring expanding test for $D \leq 114,3$ mm and $T \leq 12,5$ mm	One test per sample tube	8.3, 10.2.2.4 11.6 and 11.7	X	X
	Leak tightness test C (see Options 7 and 14)	Each tube	8.4.3.1 and 11.9	X	X
	Dimensional inspection		11.10	X	X
	Visual examination		11.11	X	X
	NDT on the weld for the detection of longitudinal imperfections		8.4.3.2 and 11.12.1	X	
	NDT on the tube body and on the weld for the detection of longitudinal imperfections		8.4.3.2 and 11.12.2		X
	Material identification check for steel grade 16Mo3	One tube per test unit	11.13		X
Optional Tests	Product analysis (Option 3)	One per cast	8.2.2, 10.2.1 and 11.1	X	X
	Verification of impact properties (Option 4)	One set of tests per sample tube	8.3, 10.2.2.5 and 11.8	X	X
	Additional longitudinal impact test at -10°C for non-alloy steels (Option 5)		8.3, Table 4, 10.2.2.5 and 11.8	X	X
	Verification of proof stress at elevated temperature (Option 6)	One test per sample tube	8.3 and 11.2.2	X	X
	NDT for the detection of transverse imperfections (Option 8)	Each tube	8.4.3.2 and 11.12.3		X
	NDT for the detection of laminar imperfections (Option 9)		8.4.3.2 and 11.12.4		X

Type of inspection and test		Frequency of testing	Refer to	Test category	
				1	2
	Transverse tensile test on the weld at room temperature for tubes with outside diameter $D > 219,1 \text{ mm OD}$ (Option 13)	One test per sample tube	11.3	X	X
	Alternative hydrostatic test pressure for leak tightness assessment (Option 14)	Each tube	11.9.1	X	X
	Wall thickness measurement away from tube end (Option 15)	Each tube	11.10	X	X
a For the flattening test, two tests shall be carried out, one with the weld positioned at 0° and one with the weld at 90°. b The choice of flattening test or ring tensile test and of drift expanding test or ring expanding test, where applicable, is at the discretion of the manufacturer. c Where the manufacturer normally uses an electromagnetic test to assess leak tightness, Option 14 will only apply if the purchaser has specified hydrostatic testing in conjunction with Option 7.					

10 Sampling

10.1 Frequency of tests

10.1.1 Test unit

For tubes delivered in conditions NR or NW (see Table 1) a test unit shall comprise tubes of the same specified diameter and wall thickness, the same steel grade, the same cast, the same manufacturing process.

For tubes delivered in condition NP (see Table 1) a test unit shall comprise tubes of the same specified diameter and wall thickness, the same steel grade, the same cast, the same manufacturing process, subjected to the same finishing treatment in a continuous furnace or heat treated in the same furnace charge in a batch-type furnace.

The maximum number of tubes per test unit shall conform to Table 11:

Table 11—Test unit details

Outside diameter D (mm)	Maximum number of tubes per test unit
$D \leq 114,3$	200
$114,3 < D \leq 323,9$	100
$D > 323,9$	50

10.1.2 Number of sample tubes per test unit

The following number of sample tubes shall be selected from each test unit:

- test category 1: one sample tube;
- test category 2: two sample tubes; when the total number of tubes is less than 20, only one sample tube shall be taken.

10.2 Preparation of samples and test pieces

10.2.1 Selection and preparation of samples for product analysis

When Option 3 is specified, one product analysis sample per cast shall be taken in accordance with EN ISO 14284. The product analysis can be carried out either on the sample tube, at the same location as for the mechanical test samples, or on the test pieces or samples after mechanical testing.

10.2.2 Location, orientation and preparation of samples and test pieces for mechanical tests

10.2.2.1 General

Samples and test pieces shall be taken at the tube ends and in accordance with the requirements of EN ISO 377.

10.2.2.2 Test pieces for tensile tests on the tube body

The test piece for the tensile test at room temperature shall be prepared in accordance with the requirements of EN ISO 6892-1.

The test piece for the proof stress test at elevated temperature shall be prepared in accordance with the requirements of EN ISO 6892-2.

At the manufacturer's discretion:

- for tubes with an outside diameter $D < 219,1$ mm, the test piece shall be either a full tube section or a strip section and shall be taken in a direction longitudinal to the axis of the tube;
- for tubes with an outside diameter $D \geq 219,1$ mm the test piece shall either a machined test piece with circular cross section from an un-flattened sample or a strip section and shall be taken in a direction either longitudinal or transverse to the axis of the tube.

Except when a full tube section is used the test piece shall be taken diametrically opposite the weld.

10.2.2.3 Test pieces for tensile tests on the weld

Samples shall be taken transverse to the weld with the weld at the centre of the test piece. The test piece shall be a strip section with the full wall thickness of the tube; any remnant of the internal weld bead may be removed.

10.2.2.4 Test pieces for flattening test, ring tensile test, drift expanding test, ring expanding test

The test piece for the flattening, ring tensile, drift expanding, ring expanding tests shall consist of a full tube section in accordance with EN ISO 8492, EN ISO 8496, EN ISO 8493 or EN ISO 8495 respectively.

10.2.2.5 Test pieces for impact tests on the tube body

Three standard Charpy V-notch test pieces shall be prepared in accordance with EN ISO 148-1. Unless otherwise specified (see Option 5, Table 4), the test pieces shall be taken transverse to the tube axis.

The test pieces shall be taken diametrically opposite the weld.


If the tube specified wall thickness is such that standard width test pieces cannot be produced without flattening of the section, then test pieces of standard width less than 10 mm, but not less than 5 mm shall be prepared; the largest obtainable standard width, either 7,5 mm or 5 mm, shall be used.

For guidance, transverse test pieces shall be taken unless D_{min} , as calculated by the following equation, is greater than the specified tube outside diameter, in which case longitudinal test pieces shall be used.

$$D_{min} = (T-5) + [756,25 / (T-5)] \quad (2)$$

Where the dimensions of the tube is such that 5mm wide longitudinal test pieces cannot be obtained, the tubes shall not be subjected to impact testing.

The test pieces shall be prepared such that the axis of the notch is through thickness, perpendicular to the surface of the tube, see Figure 3.

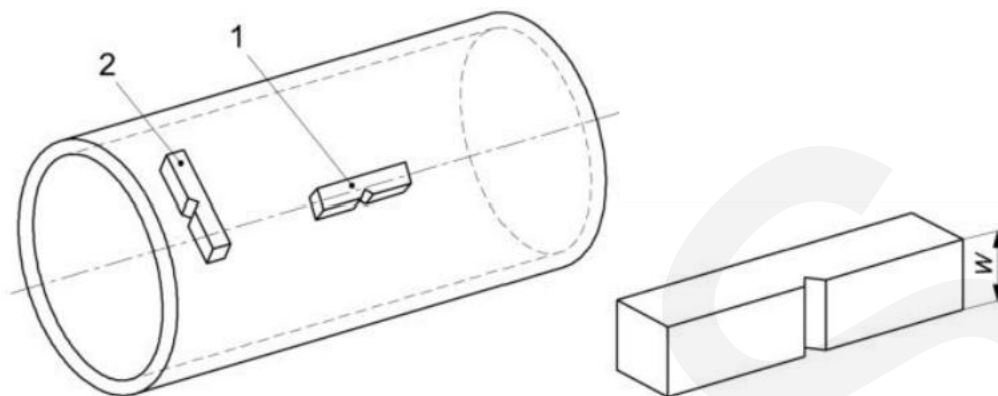

Key

- 1 longitudinal test piece
- 2 transverse test piece
- W specimen width

Figure 3—Impact test piece orientation

11 Verification of test methods

11.1 Chemical analysis

The elements to be determined and reported shall be those specified in Table 2. The choice of a suitable physical or the chemical analytical method for the analysis shall be at the discretion of the steel, strip or tube manufacturer. If further clarification is required, relevant test methods in accordance with CEN/TR10261 shall be agreed between the manufacturer and purchaser.

11.2 Tensile test on the tube body

11.2.1 At room temperature

The test shall be carried out at room temperature in accordance with EN ISO 6892-1, and the following determined:

- the tensile strength (R_m);
- the upper yield strength (R_{eH}) or if a yield phenomenon is not present the 0,2% proof strength ($R_{p0,2}$);

the percentage elongation after fracture with a reference to a gauge length (L_0) of $5,65 \cdot \sqrt{S_0}$; if a non-proportional test piece is used, the percentage elongation value shall be converted to the value for a gauge length of $5,65 \cdot \sqrt{S_0}$ using the conversion tables in EN ISO 2566-1.

11.2.2 At elevated temperature

The test shall be carried out in accordance with EN ISO 6892-2, at one temperature from Table 5 agreed at the time of enquiry and order (see 6.2), and the proof strength ($R_{p0,2}$) shall be determined.

11.3 Transverse tensile test on the weld

This is applicable to tubes of $D > 219,1$ mm, if Option 13 applies (see Table 10). The test shall be carried out in accordance with EN ISO 6892-1 except that only the tensile strength (R_m) shall be determined. The tube weld will pass the test if the result obtained exceeds the minimum R_m value specified in Table 4. The maximum R_m value does not apply in this case.

11.4 Flattening test

The test shall be carried out in accordance with EN ISO 8492. The tube section shall be flattened in a press until the distance H between the platens reaches the value given by the following Formula (3):

$$H = \frac{(1+C)}{C+(T/D)} \times T \quad (3)$$

where

H is the distance between platens, in mm, to be measured under load;

D is the specified outside diameter, in mm;

T is the specified wall thickness, in mm;

C is the deformation factor, the value of which is:

0,09 for P195GH and P235GH;

0,07 for P265GH and 16Mo3.

Two samples shall be tested, one with the weld at 0° and the other with the weld at 90° . After testing, the test piece shall be free from cracks or breaks. However, slight incipient cracks at the edges shall not be regarded as justification for rejection.

11.5 Ring tensile test

The test is applicable to tubes having an outside diameter > 150 mm and a wall thickness ≤ 40 mm.

The test shall be carried out in accordance with EN ISO 8496. The tube section shall be subjected to strain in the circumferential direction until fracture occurs.

After fracture the test pieces shall not display any cracks visible without the use of magnifying aids, excluding the fracture point.

11.6 Drift expanding test

This test is applicable to HFW tubes of outside diameter ≤ 150 mm and wall thickness ≤ 10 mm.

The test shall be carried out in accordance with EN ISO 8493. The tube section shall be expanded with a 60 conical tool until the percentage increase in outside diameter shown in Table 12 is reached.

Table 12—Drift expanding test requirements

Steel grade	Steel number	%increase in outside diameter for d/D _a		
		≤0,6	>0,6 ≤0,8	>0,8
P195GH	1.0348	12	15	19
P235GH	1.0345	10	12	17
P265GH	1.0425	8	10	15
16Mo3	1.5415	8	10	15
a d=D-2T				

After testing, the test piece shall be free from cracks or breaks. However, slight incipient cracks at the edges shall not be regarded as justification for rejection.

11.7 Ring expanding test

This test is applicable to tubes of outside diameter $18 \text{ mm} < D \leq 150 \text{ mm}$ and wall thickness $2 \text{ mm} < T \leq 16 \text{ mm}$.

The test shall be carried out in accordance with EN ISO 8495. The tube section shall be expanded with a conical tool until it breaks. The surface outside the fracture zone shall be free from cracks or breaks. However, slight incipient cracks at the edges shall not be regarded as justification for rejection.

11.8 Impact test

11.8.1 Testing shall be carried out in accordance with EN ISO 148-1, using a 2 mm radius striker, at the test temperature given in Table 4.

11.8.2 The mean value of each set of three test pieces shall meet the KV_2 requirement given in Table 4. One individual test result may be below the specified requirement, provided that it is not less than 70% of that value.

11.8.3 If the width (W) of the test piece is less than 10 mm, the measured impact energy values (KV_p) shall be converted to equivalent calculated impact energy values (KV_c) using the following Formula (4):

$$KV_c = \frac{10 \times KV_p}{W} \quad (4)$$

where

KV_c is the calculated impact energy, in Joules;

KV_p is the measured impact energy, in Joules;

W is the width of the test piece, in mm.

The mean calculated impact energy values KV_c shall conform to the requirements given in 11.8.2.

11.8.4 If the requirements of 11.8.2 are not met, then an additional set of three test pieces may be taken at the discretion of the manufacturer from the same sample tube and tested. To consider the test unit as conforming after testing the second set, the following conditions shall be satisfied simultaneously:

—the average of the six test results shall be equal to or greater than the specified minimum average value;

—not more than two of the six individual test results may be lower than the specified minimum average value;

—not more than one of the six individual test results may be lower than 70% of the specified minimum average value.

11.8.5 The dimensions in millimetres of the test pieces, the actual impact test results and the resulting average value shall be reported in the inspection certificate.

11.9 Leak tightness test

11.9.1 Hydrostatic test

Unless Option 14 is specified, the hydrostatic test shall be carried out at a test pressure of 70 bar²⁾ or at a test pressure P calculated using the following equation, whichever is lower:

$$P = 20 \times \frac{S \times T}{D} \quad (5)$$

where

P is the test pressure, in bar;

D is the specified outside diameter, in mm;

T is the specified wall thickness, in mm;

S is the stress, in MPa, corresponding to 70% of the specified minimum yield strength (see Table 4) for the steel grade concerned.

The test pressure shall be held for not less than 5 s for tubes with an outside diameter $D \leq 457$ mm and for not less than 10 s for tubes with an outside diameter $D > 457$ mm.

The tubes shall withstand the test without showing leakage.

Option 14: A test pressure different from that specified above and corresponding to a stress $< 90\%$ of the specified minimum yield strength (see Table 4) for the steel grade concerned is agreed at the time of enquiry and order.

NOTE This hydrostatic leak-tightness test is not a strength test.

11.9.2 Electromagnetic test

The test shall be carried out in accordance with EN ISO 10893-1.

11.10 Dimensional inspection

Specified dimensions, including straightness, shall be verified.

The outside diameter shall be measured at the tube ends. For tubes with outside diameter $D \geq 406,4$ mm, the diameter may be measured using a circumference tape.

Unless Option 15 is specified the wall thickness shall also be measured at the tube ends.

Option 15: The wall thickness shall be measured away from the tube ends in accordance with an agreed procedure.

²⁾ 1 bar = 100 Kpa

11.11 Visual examination

Tubes shall be visually examined to ensure conformity to the requirements of 8.4.1 and 8.4.2.1.

11.12 Non-Destructive Testing

11.12.1 The full length of the weld seam of tubes of test category 1 shall be tested in accordance with one of the following

- EN ISO 10893-2 to acceptance level E3 or E3H;
- EN ISO 10893-3 to acceptance level F3;
- EN ISO 10893-10 to acceptance level U3 sub category C;
- EN ISO 10893-11 to acceptance level U3.

Where the testing procedure is not capable of assessing the weld seam at the tube ends, then this area shall either be subjected to manual/semi-automatic ultrasonic testing in accordance with EN ISO 10893-11:2011, Annex A, or equivalent, or shall be cropped off.

Unless Option 16 is specified, the selection of test method is at the discretion of the manufacturer.

Option 16: *The test method is specified by the purchaser.*

11.12.2 Tubes of test category 2 shall be tested in accordance with one of the following:

- EN ISO 10893-3 to acceptance level F2;
- EN ISO 10893-10 for longitudinal imperfections to acceptance level U2 sub-category C.

Regions at the tube ends not automatically tested shall either be subjected to manual/semi-automatic ultrasonic testing in accordance with EN ISO 10893-10:2011, Annex B or shall be cropped off.

Unless Option 17 is specified, the selection of test method is at the discretion of the manufacturer.

Option 17: *The test method is specified by the purchaser.*

11.12.3 When Option 8 (see 8.4.3.2) is specified, tubes of test category 2 shall also be subjected to ultrasonic testing for the detection of transverse imperfections in accordance with EN ISO 10893-10 to acceptance level U2, sub-category C.

11.12.4 When Option 9 (see 8.4.3.2) is specified, tubes of test category 2 shall also be subjected to ultrasonic testing for the detection of laminar imperfections in accordance with EN ISO 10893-8 to acceptance level U2.

11.13 Material identification

Tubes made from steel grade 16Mo3 shall be tested to ensure that the correct grade is being supplied (see Table 10).

11.14 Retests, sorting and reprocessing

For retests, sorting and reprocessing the requirements of EN 10021 shall apply.

12 Marking

12.1 Marking to be applied

At least one end of each tube shall be indelibly marked by a suitable and durable method, such as an automated ink or paint marking process, paint stencil or hard stamping (using low stress or pin stamps) or a combination of these.

The marking shall include the following information:

- the manufacturer's name or trade mark or product brand;
- the type of tube (HFW);
- the number of this document (EN 10217-2);
- the steel name or steel number (see 5.2.1 and 5.2.2 or 5.2.3);
- the designation of test category in the case of non-alloy steel grades (see 9.3);
 - the cast number and/or an identification number (e.g. an order or item number or manufacturing reference code) which permits correlation of the product or delivery unit to the related documentation;
- the mark of the inspection representative, if applicable.

For tubes with outside diameter $D \leq 51$ mm the marking on the tubes may be replaced by marking on a label or tag, which shall be securely attached to the bundle or box. Additionally, the label or tag shall identify the tube diameter, wall thickness and length range.

NOTE Example of marking:

X-HFW-EN 10217-2—P265GH-TC1—Y-Z

where

- X is the manufacturer's mark;
- HFW is the type of tube;
- TC1 is the test category;
- Y is the cast number or identification number or a code number;
- Z is the mark of the inspection representative, if applicable;

12.2 Additional marking

Unless Option 18 is specified, no additional marking other than that specified in 12.1 need be applied.

Option 18: Additional marking, as agreed upon at the time of enquiry and order, shall be applied.

13 Protection

Unless Option 19 is specified, the tubes shall be delivered without any protective coating.

Option 19: A temporary protective coating or durable coating and/or lining shall be applied.

Annex A (informative)

Technical changes from the previous edition

A.1 Introduction

This informative annex is intended to guide the user to places where significant technical changes have been introduced into the previous edition of this European Standard. Editorial changes are not included in this annex. References refer to the previous edition.

While this annex is intended to be comprehensive, users should satisfy themselves that they fully understand the changes which have been made. The user is ultimately responsible for recognizing any differences between this edition and the previous edition of the document.

A.2 Technical changes

- 1 Scope
- 2 Normative references
- 3 Terms and definitions
- 4 Symbols
- 6 Information to be supplied by the purchaser
 - 6.2 Options [4], [5], [6], [7], [12], [13], [16] and [17]
 - 6.3 Example of an order
- 7 Manufacturing process
 - 7.1 Steelmaking process
 - 7.2 Tube manufacture and delivery conditions
 - Table 1
 - 7.3 Non-destructive testing personnel requirements
- 8 Requirements
 - 8.1 General
 - Table 2
 - 8.3 Mechanical properties
 - Table 4
 - Table 5

- 8.4 Appearance and internal soundness
- 8.6 Preparation of ends
- 8.7 Dimensions mass and tolerances
- 9 Inspections
 - 9.1 Types of inspections
 - 9.2 Inspection documents
 - 9.3 Summary of inspection and testing
 - Table 10
- 10 Sampling
 - 10.1 Frequency of tests (Table 11)
 - 10.2 Preparation of samples and test pieces
- 11 Verification test methods
 - 11.1 Chemical analysis
 - 11.3 Transverse tensile test on the weld
 - 11.5 Ring tensile test
 - 11.6 Drift expanding test
 - Table 12
 - 11.7 Ring expanding test
 - 11.8 Impact test
 - 11.9 Leak tightness test
 - 11.10 Dimensional inspection
 - 11.11 Visual examination
 - 11.12 Non-destructive testing
- 12 Marking
- Annex ZA

Annex ZA (informative)

Relationship between this European Standard and the Essential Requirements of 2014/68/EU

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association to provide a means of conforming to Essential Requirements of the New Approach Directive formerly 2014/68/EU.

Once this standard is cited in the Official Journal of the European Union under that Directive and has been implemented as a national standard in at least one Member State, compliance with the clauses of this standard given in Table ZA.1 confers, within the limits of the scope of this standard, a presumption of conformity with the corresponding Essential Requirements of that Directive and associated EFTA regulations:

**Table ZA.1—Correspondence between this European Standard and Annex I of the Directive
2014/68/EU**

Essential Requirements of the Directive 2014/68/EU	Clauses/sub-clauses of this EN	Remarks/Notes
3.1.2	7.2.2	Welding For the HFW tubes used for pressure equipment in categories II, III and IV, the operating procedures and the personnel shall be approved by a notified body or a recognized third party organisation.
3.1.3	7.3	NDT personnel requirements For tubes to be used in pressure equipment under Categories II and IV the personnel shall be approved by a recognised third party organisation.
4.1. a	8.3	Appropriate material properties
4.1. c	7.1 and 8.2	Ageing
4.1. d	7.2.1, 7.2.3, 8.4	Suitable for the processing procedures.
4.3	Clause 9	Inspection documentation.

WARNING1— Presumption of conformity stays valid only as long as a reference to this European Standard is maintained in the list published in the Official Journal of the European Union. Users of this standard should consult frequently the latest list published in the Official Journal of the European Union.

WARNING2— Other Union legislation may be applicable to the products falling within the scope of this standard.

Bibliography

EN ISO 9712, Non-destructive testing—Qualification and certification of NDT personnel (ISO 9712)

British Standards Institution(BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
 - The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
 - A single paper copy may be printed for personal or internal company use only.
- Standards purchased in hard copy format:
- A British Standard purchased in hard copy format is for personal or internal company use only.
 - It may not be further reproduced - in any format - to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over **55,000** British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Mult-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email subscriptions@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision. We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +443450869001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +443450869001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +442089967004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +442089967070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W44AL UK