

Copper and copper alloys — Seamless, round tubes for general purposes



www.dlsspipeline.com

info@dlsspipe.com

The European Standard EN 12449:1999 has the status of a British Standard

ICS 23.040.15; 77.150.30

National foreword

This British Standard is the English language version of EN 12449:1999. It supersedes BS 2871-2:1972 which is withdrawn.

The UK participation in its preparation was entrusted by Technical Committee NFE/34, Copper and copper alloys, to Subcommittee NFE/34/1, Wrought and unwrought copper and copper alloys, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this subcommittee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the BSI Standards Catalogue under the section entitled “International Standards Correspondence Index”, or by using the “Find” facility of the BSI Standards Electronic Catalogue.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 37 and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

This British Standard, having been prepared under the direction of the Engineering Sector Committee, was published under the authority of the Standards Committee and comes into effect on 15 November 1999

© BSI 11-1999

Amendments issued since publication

Amd. No.	Date	Comments

ICS 23.040.15; 77.120.30

English version

Copper and copper alloys — Seamless, round tubes for general purposes

Cuivre et alliages de cuivre — Tubes ronds sans soudure
pour usages généraux

Kupfer und Kupferlegierungen — Nahtlose Rundrohre zur
allgemeinen Verwendung

This European Standard was approved by CEN on 26 May 1999.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.


cen

EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Central Secretariat: rue de Stassart 36, B-1050 Brussels

Contents

	Page		Page
Foreword	3	Table 6: Composition of binary copper-zinc alloys	14
1 Scope	4	Table 7: Composition of copper-zinc-lead alloys	15
2 Normative references	4	Table 8: Composition of complex copper-zinc alloys	16
3 Definitions	4	Table 9: Mechanical properties of copper and low alloyed copper alloys	17
4 Designations	5	Table 10: Mechanical properties of copper-nickel alloys	19
4.1 Material	5	Table 11: Mechanical properties of copper-nickel-zinc alloys	20
4.2 Material condition	5	Table 12: Mechanical properties of copper-tin alloys	21
4.3 Product	6	Table 13: Mechanical properties of binary copper-zinc alloys	24
5 Ordering information	6	Table 14: Mechanical properties of copper-zinc-lead alloys	28
6 Requirements	7	Table 15: Mechanical properties of complex copper-zinc alloys	31
6.1 Composition	7	Table 16: Tolerances on diameter	34
6.2 Mechanical properties	8	Table 17: Tolerances on wall thickness	34
6.3 Dimensions and tolerances	8	Table 18: Tolerances on fixed lengths, tubes in straight lengths	35
6.4 Surface quality	8	Table 19: Tolerances on fixed lengths, tube in coils (not level wound)	35
6.5 Technological requirements	9	Table 20: Tolerances on diameter including deviation from circular form, tube in coils	35
7 Sampling	9	Table 21: Tolerances on straightness	36
7.1 General	9	Table 22: Sampling rate	36
7.2 Analysis	9	Annex A (informative) Bibliography	37
7.3 Mechanical tests and stress corrosion resistance test	9		
8 Test methods	10		
8.1 Analysis	10		
8.2 Tensile test	10		
8.3 Hardness test	10		
8.4 Technological tests	10		
8.5 Freedom from defects tests	10		
8.6 Retests	11		
8.7 Rounding of results	11		
9 Declaration of conformity and inspection documentation	11		
9.1 Declaration of conformity	11		
9.2 Inspection documentation	11		
10 Marking, packaging, labelling	11		
Table 1: Composition of copper	12		
Table 2: Composition of low alloyed copper alloys	12		
Table 3: Composition of copper-nickel alloys ...	12		
Table 4: Composition of copper-nickel-zinc alloys	12		
Table 5: Composition of copper-tin alloys	13		

Foreword

This European Standard has been prepared by Technical Committee CEN/TC 133 "Copper and copper alloys", the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2000, and conflicting national standards shall be withdrawn at the latest by January 2000.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

This European Standard has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association. This European Standard is considered to be a supporting standard to those application and product standards which in themselves support an essential safety requirement of a New Approach Directive and which make reference to this European Standard.

Within its programme of work, Technical Committee CEN/TC 133 requested CEN/TC 133/WG 3.2 "Tubes for general purposes" to prepare the following standard:

EN 12449

Copper and copper alloys – Seamless, round tubes for general purposes

This is one of a series of European Standards for copper and copper alloy tubes. Other products are, or will be, specified as follows:

EN 1057

Copper and copper alloys – Seamless, round copper tubes for water and gas in sanitary and heating applications

EN 12450

Copper and copper alloys – Seamless, round copper capillary tubes

EN 12451

Copper and copper alloys – Seamless, round tubes for heat exchangers

EN 12452

Copper and copper alloys – Rolled, finned, seamless tubes for heat exchangers

prEN 12735-1

Copper and copper alloys – Seamless, round copper tubes for air conditioning and refrigeration – Part 1: Tubes for piping systems

prEN 12735-2

Copper and copper alloys – Seamless, round copper tubes for air conditioning and refrigeration – Part 2: Tubes for equipment

prEN 13348

Copper and copper alloys – Seamless, round copper tubes for medical gases

prEN 13349

Copper and copper alloys – Pre-insulated copper tubes with solid covering

prEN 13600

Copper and copper alloys – Seamless copper tubes for electrical purposes

1 Scope

This European Standard specifies the composition, property requirements and tolerances on dimensions and form for seamless round drawn copper and copper alloy tubes for general purposes supplied in the size range from 3 mm up to and including 450 mm outside diameter and from 0,3 mm up to and including 20 mm wall thickness.

The sampling procedures and the methods of test for verification of conformity to the requirements of this standard are also specified.

NOTE: Tubes having an outside diameter less than 80 mm and/or a wall thickness greater than 2 mm in certain alloys are most frequently used for the free machining purposes which are specified in EN 12168.

2 Normative references

This European Standard incorporates, by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references, the latest edition of the publication referred to applies.

EN 1655

Copper and copper alloys – Declarations of conformity

EN 10002-1

Metallic materials – Tensile testing – Part 1: Method of test (at ambient temperature)

EN 10003-1

Metallic materials – Brinell hardness test – Part 1: Test method

EN 10204

Metallic products – Types of inspection documents

EN 10234

Metallic materials – Tube – Drift expanding test

EN ISO 196

Wrought copper and copper alloys – Detection of residual stress – Mercury(I) nitrate test (ISO 196 : 1978)

EN ISO 2624

Copper and copper alloys – Estimation of average grain size (ISO 2624 : 1990)

EN ISO 6507-1

Metallic materials – Vickers hardness test – Part 1: Test method (ISO 6507-1:1997)

ISO 6957

Copper alloys – Ammonia test for stress corrosion resistance

NOTE: Informative references to documents used in the preparation of this standard, and cited at the appropriate places in the text, are listed in a bibliography, see annex A.

3 Definitions

For the purposes of this standard, the following definitions apply:

3.1 seamless round tube

Hollow semi-finished product, circular in cross section, having a uniform wall thickness which at all stages of production has a continuous periphery.

3.2 mean diameter

Arithmetical mean of any two diameters normal to each other at the same cross section of the tube.

3.3 deviation from circular form

Difference between the maximum and minimum outside diameters measured at any one cross section of the tube.

4 Designations

4.1 Material

4.1.1 General

The material is designated either by symbol or number (see tables 1 to 8).

4.1.2 Symbol

The material symbol designation is based on the designation system given in ISO 1190-1.

NOTE: Although material symbol designations used in this standard might be the same as those in other standards using the designation system given in ISO 1190-1, the detailed composition requirements are not necessarily the same.

4.1.3 Number

The material number designation is in accordance with the system given in EN 1412.

4.2 Material condition

For the purposes of this standard, the following designations, which are in accordance with the system given in EN 1173, apply for the material condition:

M Material condition for the product as manufactured without specified mechanical properties;

R... Material condition designated by the minimum value of tensile strength requirement for the product with mandatory tensile property requirements;

H... Material condition designated by the minimum value of hardness requirement for the product with mandatory hardness requirements.

NOTE 1: Products in the H... condition can be specified to Vickers or Brinell hardness. The material condition designation H... is the same for both hardness test methods.

S (suffix) Material condition for a product which is stress relieved.

NOTE 2: Products in the M, R... or H... condition can be specially processed (i.e. mechanically or thermally stress relieved) in order to lower the residual stress level to improve the resistance to stress corrosion (see 6.5.2).

Exact conversion between the material conditions designated R... and H... is not possible.

Except when the suffix S is used, material condition is designated by only one of the above designations.

4.3 Product

The product designation provides a standardized pattern of designation from which a rapid and unequivocal description of a product is conveyed in communication. It provides mutual comprehension at the international level with regard to products which meet the requirements of the relevant European Standard.

The product designation is no substitute for the full content of the standard.

The product designation for products to this standard shall consist of:

- denomination (Tube);
- number of this European Standard (EN 12449);
- material designation, either symbol or number (see tables 1 to 8);
- material condition designation (see tables 9 to 15);
- nominal cross-sectional dimensions, either outside diameter (OD) and wall thickness or inside diameter (ID) and wall thickness (see 6.3).


The derivation of a product designation is shown in example 1.

EXAMPLE 1:

Tube conforming to this standard, in material designated either CuNi10Fe1Mn or CW352H, in material condition H075, nominal outside diameter 22 mm, nominal wall thickness 2,0 mm, shall be designated as follows:

Tube EN 12449 – CuNi10Fe1Mn – H075 – OD22 × 2,0

or

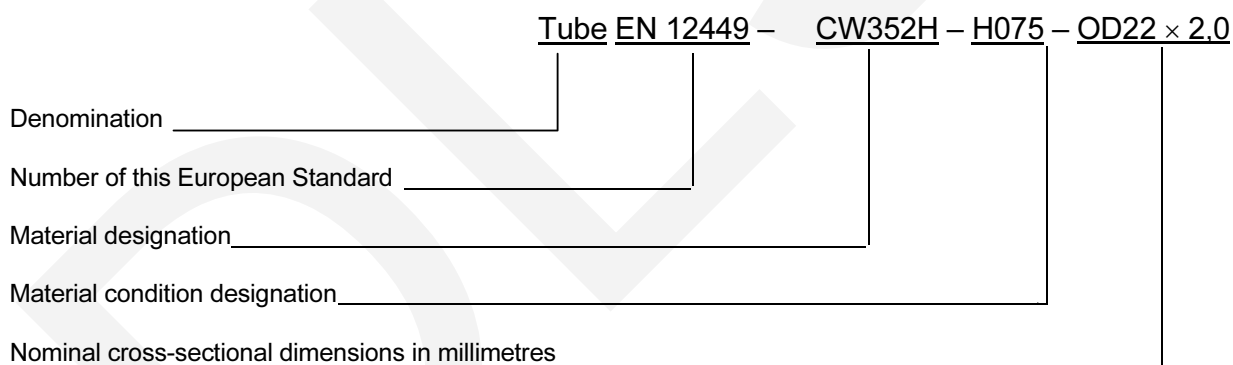

EXAMPLE 2:

Tube conforming to this standard, in material designated either CuZn37 or CW508L, in material condition M, stress relieved, nominal inside diameter 30 mm, nominal wall thickness 2,5 mm, shall be designated as follows:

Tube EN 12449 – CuZn37 – MS – ID30 × 2,5

or

Tube EN 12449 – CW508L – MS – ID30 × 2,5

5 Ordering information

In order to facilitate the enquiry, order and confirmation of order procedures between the purchaser and the supplier, the purchaser shall state on his enquiry and order the following information:

- a) quantity of product required (number of pieces, length or mass);

- b) denomination (Tube);
- c) number of this European Standard (EN 12449);
- d) material designation (see tables 1 to 8);
- e) material condition designation (see 4.2 and tables 9 to 15) if it is other than M;
- f) nominal cross-sectional dimensions [either outside diameter (OD) and wall thickness or inside diameter (ID) and wall thickness] (see 6.3);
- g) length, either nominal together with tolerance required, or fixed length (see 6.3.4);

NOTE 1: It is recommended that the product designation, as described in 4.3, is used for items b) to f).

In addition, the purchaser shall also state on the enquiry and order any of the following, if required:

- h) whether the tubes are for sea water application (see table 3). If so, the composition limits required;
- i) test method to be used for the measurement of hardness, i.e. Vickers or Brinell (see 8.3);
- j) where dimensional tolerances are to be applied, if not on the outside diameter and wall thickness (see 6.3.1);
- k) whether the tubes are required to pass a drift expanding test (see 6.5.1);
- l) whether the tubes are required to pass a stress corrosion resistance test (see 6.5.2);
- m) whether the tubes are required to meet a grain size requirement (see 6.5.3). If so, the grain size limits required;

NOTE 2: The grain size limits should be agreed between the purchaser and the supplier.

- n) whether the tubes are required to pass freedom from defects tests (see 6.5.4). If so, which test method is to be used (see 8.5), if the choice is not to be left to the discretion of the supplier, and the acceptance criteria if they are not to be left to the discretion of the supplier;
- o) whether deburring is required (see 6.4);
- p) whether special surface quality is required (see 6.4);
- q) whether a declaration of conformity is required (see 9.1);
- r) whether an inspection document is required, and if so, which type (see 9.2);
- s) whether there are any special requirements for marking, packaging or labelling (see clause 10).

EXAMPLE:

Ordering details for 1 000 m tube conforming to EN 12449, in material designated either CuNi10Fe1Mn or CW352H, in material condition H075, nominal outside diameter 22 mm, nominal wall thickness 2,0 mm, in 3 000 mm fixed lengths:

**1 000 m tube EN 12449 – CuNi10Fe1Mn – H075 – OD22 × 2,0
– fixed length 3 000 mm**

or

**1 000 m tube EN 12449 – CW352H – H075 – OD22 × 2,0
– fixed length 3 000 mm**

6 Requirements

6.1 Composition

The composition shall conform to the requirements for the appropriate material given in tables 1 to 8.

6.2 Mechanical properties

The properties shall conform to the appropriate requirements given in tables 9 to 15. The tests shall be carried out in accordance with either 8.2 (tensile test) or 8.3 (hardness test).

Products in stress relieved condition shall conform to the same mechanical property requirements as for non stress relieved material.

6.3 Dimensions and tolerances

6.3.1 General

The geometrical properties of the tubes are defined by outside diameter or inside diameter, wall thickness and length.

Normally, tolerances for cross-sectional dimensions are applied on the outside diameter (see 6.3.2) and wall thickness (see 6.3.3) but other possibilities may be agreed between the purchaser and the supplier at the time of the enquiry and order [see 5 j)].

Normally, tubes are supplied in lengths with tolerances agreed between the purchaser and the supplier at the time of the enquiry and order [see 5 g)] but tubes may be ordered as "fixed lengths" (see 6.3.4).

6.3.2 Outside or inside diameter

The diameter of the tubes shall conform to the tolerances given in table 16.

6.3.3 Wall thickness

The wall thickness, measured at any point, shall conform to the tolerances given in table 17.

6.3.4 Fixed lengths

Tubes in straight lengths ordered as "fixed lengths" shall conform to the tolerances given in table 18. Tubes in coiled form ordered as "fixed lengths" shall conform to the tolerances given in table 19.

6.3.5 Tolerances of form

6.3.5.1 Deviation from circular form

For tubes in straight lengths the deviation from circular form is included in the tolerances on diameter given in table 16.

For coiled tubes with wall thicknesses up to and including 2 mm, except for tubes with ratios of outside diameter to wall thickness greater than 20, the deviation from circular form is included in the tolerances on diameter given in table 20.

6.3.5.2 Straightness

Tubes in straight lengths, except for those in the annealed condition (see tables 9 to 15) or with outside diameter equal to or less than 10 mm, shall conform to the tolerances given in table 21.

6.4 Surface quality

The external and internal surfaces shall be clean and smooth.

The tubes may have a superficial film of drawing lubricant or, if annealed or thermally stress relieved, a superficial, dull, iridescent oxide film, securely adherent on both the internal and external surfaces.

Discontinuous irregularities on the external and internal surfaces of the tubes are permitted if they are within the dimensional tolerances.

Special requirements (e.g. pickling, degreasing, etc.) relating to the surface quality shall be agreed between the purchaser and the supplier [see 5 p)].

If deburring of the cut ends of the tubes is required it shall be agreed between the purchaser and the supplier [see 5 o)].

6.5 Technological requirements

6.5.1 Drift expanding

No crack shall be visible to the unaided eye, corrected for normal vision if necessary, when tubes in the annealed condition and outside diameter up to and including 100 mm and when agreed between the purchaser and the supplier [see 5 k)] are tested in accordance with 8.4.1.

6.5.2 Residual stress level

No crack shall be visible to the unaided eye, corrected for normal vision if necessary, when tubes in the stress relieved condition and when requested by the purchaser [see 5 l)] are tested in accordance with 8.4.2.

6.5.3 Grain size

The average grain size of tubes in the annealed condition, when requested by the purchaser, [see 5 m)] shall conform to the limits agreed between the purchaser and the supplier. The test shall be carried out in accordance with 8.4.3.

6.5.4 Freedom from defects

When requested by the purchaser [see 5 n)] tubes shall be tested in accordance with 8.5 and the acceptance criteria, unless otherwise agreed between the purchaser and the supplier, shall be at the discretion of the supplier.

7 Sampling

7.1 General

When required (e.g. if necessary in accordance with specified procedures of a supplier's quality system, or when the purchaser requests inspection documents with test results, or for use in cases of dispute), an inspection lot shall be sampled in accordance with 7.2 and 7.3.

7.2 Analysis

The sampling rate shall be in accordance with table 22. A test sample, depending on the analytical technique to be employed, shall be prepared from each sampling unit and used for the determination of the composition.

NOTE 1: When preparing the test sample, care should be taken to avoid contaminating or overheating the test sample. Carbide tipped tools are recommended; steel tools, if used, should be made of magnetic material to assist in the subsequent removal of extraneous iron. If the test samples are in finely divided form (e.g. drillings, millings), they should be treated carefully with a strong magnet to remove any particles of iron introduced during preparation.

NOTE 2: In cases of dispute concerning the results of analysis, the full procedure given in ISO 1811-2 should be followed.

Results may be used from analyses carried out at an earlier stage of manufacturing the product, e.g. at the casting stage, if the material identity is maintained and if the quality system of the manufacturer is certified as conforming to EN ISO 9001 or EN ISO 9002.

7.3 Mechanical tests and stress corrosion resistance test

The sampling rate shall be in accordance with table 22. Sampling units shall be selected from the finished products. The test samples shall be cut from the sampling units. Test samples, and test pieces prepared from them, shall not be subjected to any further treatment, other than any machining operations necessary in the preparation of the test pieces.

8 Test methods

8.1 Analysis

Analysis shall be carried out on the test pieces, or test portions, prepared from the test samples obtained in accordance with 7.2. Except in cases of dispute, the analytical methods used shall be chemical or spectrographic according to ISO standards in force. For expression of results, the rounding rules given in 8.7 shall be used.

NOTE: In cases of dispute concerning the results of analysis, the method of analysis to be used should be chemical.

8.2 Tensile test

The tensile properties shall be determined in accordance with EN 10002-1 on the test pieces obtained in accordance with 7.3.

8.3 Hardness test

Hardness shall be determined on test pieces prepared from the test samples obtained in accordance with 7.3. The test shall be carried out in accordance with either EN 10003-1 or EN ISO 6507-1 and the impression/indentation made on the outside surface, unless otherwise agreed. For the Brinell test according to EN 10003-1 a $0,102 F/D^2$ ratio of 10 shall be used.

8.4 Technological tests

8.4.1 Drift expanding test

When required, the drift expanding test shall be carried out in accordance with EN 10234. The outside diameter of the tube end shall be expanded by 30 % using a conical mandrel with an angle of 45°.

8.4.2 Stress corrosion resistance test

When required, the test method given in either EN ISO 196 or ISO 6957 shall be used on the test pieces prepared from the test samples obtained in accordance with 7.3. The choice of which of these tests is used shall be at the discretion of the supplier.

8.4.3 Average grain size determination

When required, the estimation of average grain size shall be carried out in accordance with EN ISO 2624.

8.5 Freedom from defects tests

When required, each tube shall be subjected to one of the following tests:

- Eddy current test;
- Hydrostatic test;
- Pneumatic test.

If not otherwise agreed between the purchaser and the supplier, the test method to be used and the method of testing shall be at the discretion of the manufacturer.

8.6 Retests

8.6.1 Analysis, tensile, hardness, drift expanding and grain size tests

If there is a failure of one, or more than one, of the tests in 8.1, 8.2, 8.3, 8.4.1 or 8.4.3, two test samples from the same inspection lot shall be permitted to be selected for retesting the failed property (properties). One of these test samples shall be taken from the same sampling unit as that from which the original failed test piece was taken, unless that sampling unit is no longer available, or has been withdrawn by the supplier.

If the test pieces from both test samples pass the appropriate test(s), then the inspection lot represented shall be deemed to conform to the particular requirement(s) of this standard. If a test piece fails a test, the inspection lot represented shall be deemed not to conform to this standard.

8.6.2 Stress corrosion resistance test

If a test piece fails the test, the inspection lot represented by the failed test piece shall be permitted to be subjected to a stress relieving treatment. A further test sample shall then be selected in accordance with 7.3.

If a test piece from the further test sample passes the test, the stress relieved material shall be deemed to conform to the requirements of this standard for residual stress level and shall then be subjected to all the other tests called for on the purchase order, except for analysis. If the test piece from the further test sample fails the test, the stress relieved material shall be deemed not to conform to this standard.

8.7 Rounding of results

For the purpose of determining conformity to the limits specified in this standard, an observed or a calculated value obtained from a test shall be rounded in accordance with the following procedure, which is based upon the guidance given in annex B of ISO 31-0 : 1992. It shall be rounded in one step to the same number of figures used to express the specified limit in this standard, except that for tensile strength and 0,2 % proof strength where the rounding interval shall be 10 N/mm², and for elongation the value shall be rounded to the nearest 1 %.

The following rules shall be used for rounding:

- a) if the figure immediately after the last figure to be retained is less than 5, the last figure to be retained shall be kept unchanged;
- b) if the figure immediately after the last figure to be retained is equal to or greater than 5, the last figure to be retained shall be increased by one.

9 Declaration of conformity and inspection documentation

9.1 Declaration of conformity

When requested by the purchaser [see 5 q)] and agreed with the supplier, the supplier shall issue for the products the appropriate declaration of conformity in accordance with EN 1655.

9.2 Inspection documentation

When requested by the purchaser [see 5 r)] and agreed with the supplier, the supplier shall issue for the products the appropriate inspection document in accordance with EN 10204.

10 Marking, packaging, labelling

Unless otherwise specified by the purchaser and agreed by the supplier, the marking, packaging and labelling shall be left to the discretion of the supplier [see 5 s)].

Table 1: Composition of copper

Material designation		Composition in % (m/m)			Density ¹⁾ g/cm ³ approx.
Symbol	Number	Element	Cu ¹⁾	P	
Cu-DHP	CW024A	min. max.	99,90 –	0,015 0,040	8,9

¹⁾ Including Ag, up to a maximum of 0,015 %.

²⁾ For information only.

Table 2: Composition of low alloyed copper alloys

Material designation		Composition in % (m/m)										Density ¹⁾ g/cm ³ approx.
Symbol	Number	Element	Cu	Fe	Mn	Ni	P	Pb	Si	Zn	Others total	
CuFe2P	CW107C	min. max.	Rem. –	2,1 2,6	– –	– –	0,015 0,15	– 0,03	– –	0,05 0,20	– 0,2	8,8
CuNi2Si	CW111C	min. max.	Rem. –	– 0,2	– 0,1	1,6 2,5	– –	– 0,02	0,4 0,8	– –	– 0,3	8,8

¹⁾ For information only.

Table 3: Composition of copper-nickel alloys

Material designation		Composition in % (m/m)													Density ¹⁾ g/cm ³ approx.
Symbol	Number	Element	Cu	C	Co	Fe	Mn	Ni	P	Pb	S	Sn	Zn	Others total	
CuNi10Fe1Mn	CW352H	min. max.	Rem. –	– 0,05	– 0,1 ²⁾	1,0 ²⁾ 2,0 ²⁾	0,5 1,0	9,0 11,0	– 0,02	– 0,02	– 0,05	– 0,03	– 0,5	– 0,2	8,9
CuNi30Mn1Fe	CW354H	min. max.	Rem. –	– 0,05	– 0,1 ²⁾	0,4 1,0	0,5 1,5	30,0 32,0	– 0,02	– 0,02	– 0,05	– 0,05	– 0,5	– 0,2	8,9

¹⁾ For information only.

²⁾ Co max. 0,1 % is counted as Ni.

³⁾ For sea water applications, the composition limits shall be agreed between the purchaser and the supplier [see 5 h)].

Table 4: Composition of copper-nickel-zinc alloys

Material designation		Composition in % (m/m)									Density ¹⁾ g/cm ³ approx.
Symbol	Number	Element	Cu	Fe	Mn	Ni	Pb	Sn	Zn	Others total	
CuNi12Zn24	CW403J	min. max.	63,0 66,0	– 0,3	– 0,5	11,0 13,0	– 0,03	– 0,03	Rem. –	– 0,2	8,7
CuNi18Zn20	CW409J	min. max.	60,0 63,0	– 0,3	– 0,5	17,0 19,0	– 0,03	– 0,03	Rem. –	– 0,2	8,7

¹⁾ For information only.

Table 5: Composition of copper-tin alloys

Material designation		Composition in % (m/m)									Density ¹⁾ g/cm ³ approx.
Symbol	Number	Element	Cu	Fe	Ni	P	Pb	Sn	Zn	Others total	
CuSn6	CW452K	min. max.	Rem. –	– 0,1	– 0,2	0,01 0,4	– 0,02	5,5 7,0	– 0,2	– 0,2	8,8
CuSn8	CW453K	min. max.	Rem. –	– 0,1	– 0,2	0,01 0,4	– 0,02	7,5 8,5	– 0,2	– 0,2	8,8
CuSn4Pb2P	CW455K	min. max.	Rem. –	– 0,1	– 0,2	0,2 0,4	1,5 2,5	3,5 4,5	– 0,3	– 0,2	8,9
CuSn8P	CW459K	min. max.	Rem. –	– 0,1	– 0,3	0,2 0,4	– 0,05	7,5 8,5	– 0,3	– 0,2	8,8
CuSn8PbP	CW460K	min. max.	Rem. –	– 0,1	– 0,3	0,2 0,4	0,1 0,5	7,5 9,0	– 0,3	– 0,2	8,8

¹⁾ For information only.

Table 6: Composition of binary copper-zinc alloys

Material designation		Composition in % (m/m)									Density ¹⁾ g/cm ³ approx.
Symbol	Number	Element	Cu	Al	Fe	Ni	Pb	Sn	Zn	Others total	
CuZn5	CW500L	min. max.	94,0 96,0	— 0,02	— 0,05	— 0,3	— 0,05	— 0,1	Rem. —	— 0,1	8,9
CuZn10	CW501L	min. max.	89,0 91,0	— 0,02	— 0,05	— 0,3	— 0,05	— 0,1	Rem. —	— 0,1	8,8
CuZn15	CW502L	min. max.	84,0 86,0	— 0,02	— 0,05	— 0,3	— 0,05	— 0,1	Rem. —	— 0,1	8,8
CuZn20	CW503L	min. max.	79,0 81,0	— 0,02	— 0,05	— 0,3	— 0,05	— 0,1	Rem. —	— 0,1	8,7
CuZn30	CW505L	min. max.	69,0 71,0	— 0,02	— 0,05	— 0,3	— 0,05	— 0,1	Rem. —	— 0,1	8,5
CuZn36	CW507L	min. max.	63,5 65,5	— 0,02	— 0,05	— 0,3	— 0,05	— 0,1	Rem. —	— 0,1	8,4
CuZn37	CW508L	min. max.	62,0 64,0	— 0,05	— 0,1	— 0,3	— 0,1	— 0,1	Rem. —	— 0,1	8,4
CuZn40	CW509L	min. max.	59,5 61,5	— 0,05	— 0,2	— 0,3	— 0,3	— 0,2	Rem. —	— 0,2	8,4

¹⁾ For information only.

Table 7: Composition of copper-zinc-lead alloys

Material designation		Composition in % (m/m)											Density ¹⁾ g/cm ³ approx.
Symbol	Number	Element	Cu	Al	As	Fe	Mn	Ni	Pb	Sn	Zn	Others total	
CuZn35Pb1	CW600N	min. max.	62,5 64,0	— 0,05	— —	— 0,1	— —	— 0,3	0,8 1,6	— 0,1	Rem. —	— 0,1	8,5
CuZn35Pb2 ²⁾	CW601N ²⁾	min. max.	62,0 63,5	— 0,05	— —	— 0,1	— —	— 0,3	1,6 2,5	— 0,1	Rem. —	— 0,1	8,5
CuZn36Pb2As ²⁾	CW602N ²⁾	min. max.	61,0 63,0	— 0,05	0,02 0,15	— 0,1	— 0,1	— 0,3	1,7 2,8	— 0,1	Rem. —	— 0,2	8,4
CuZn36Pb3 ²⁾	CW603N ²⁾	min. max.	60,0 62,0	— 0,05	— —	— 0,3	— —	— 0,3	2,5 3,5	— 0,2	Rem. —	— 0,2	8,5
CuZn37Pb0,5	CW604N	min. max.	62,0 64,0	— 0,05	— —	— 0,1	— —	— 0,3	0,1 0,8	— 0,2	Rem. —	— 0,2	8,4
CuZn37Pb1 ²⁾	CW605N ²⁾	min. max.	61,0 62,0	— 0,05	— —	— 0,2	— —	— 0,3	0,8 1,6	— 0,2	Rem. —	— 0,2	8,4
CuZn38Pb1 ²⁾	CW607N ²⁾	min. max.	60,0 61,0	— 0,05	— —	— 0,2	— —	— 0,3	0,8 1,6	— 0,2	Rem. —	— 0,2	8,4
CuZn38Pb2 ²⁾	CW608N ²⁾	min. max.	60,0 61,0	— 0,05	— —	— 0,2	— —	— 0,3	1,6 2,5	— 0,2	Rem. —	— 0,2	8,4
CuZn39Pb3 ²⁾	CW614N ²⁾	min. max.	57,0 59,0	— 0,05	— —	— 0,3	— —	— 0,3	2,5 3,5	— 0,3	Rem. —	— 0,2	8,4
CuZn40Pb2 ²⁾	CW617N ²⁾	min. max.	57,0 59,0	— 0,05	— —	— 0,3	— —	— 0,3	1,6 2,5	— 0,3	Rem. —	— 0,2	8,4
¹⁾ For information only.													
²⁾ See note to clause 1.													

Table 8: Composition of complex copper-zinc alloys

Material designation		Composition in % (m/m)													Density ^{††} g/cm ³ approx.
Symbol	Number	Element	Cu	Al	As	Fe	Mn	Ni	P	Pb	Si	Sn	Zn	Others total	
CuZn13Al1Ni1Si1	CW700R	min. max.	81,0 84,0	0,7 1,2	– –	– 0,25	– 0,1	0,8 1,4	– –	– 0,05	0,8 1,3	– 0,1	Rem. –	– 0,5	8,5
CuZn20Al2As	CW702R	min. max.	76,0 79,0	1,8 2,3	0,02 0,06	– 0,07	– 0,1	– 0,1	– 0,01	– 0,05	– –	– –	Rem. –	– 0,3	8,4
CuZn31Si1	CW708R	min. max.	66,0 70,0	– –	– –	– 0,4	– –	– 0,5	– –	– 0,8	0,7 1,3	– –	Rem. –	– 0,5	8,4
CuZn35Ni3Mn2AlPb	CW710R	min. max.	58,0 60,0	0,3 1,3	– –	– 0,5	1,5 2,5	2,0 3,0	– –	0,2 0,8	– 0,1	– 0,5	Rem. –	– 0,3	8,3
CuZn37Mn3Al2PbSi ^{‡‡}	CW713R ^{‡‡}	min. max.	57,0 59,0	1,3 2,3	– –	– 1,0	1,5 3,0	– 1,0	– –	0,2 0,8	0,3 1,3	– 0,4	Rem. –	– 0,3	8,1
CuZn38Mn1Al	CW716R	min. max.	59,0 61,5	0,3 1,3	– –	– 1,0	0,6 1,8	– 0,6	– –	– 1,0	– 0,5	– 0,3	Rem. –	– 0,3	8,3
CuZn39Mn1AlPbSi	CW718R	min. max.	57,0 59,0	0,3 1,3	– –	– 0,5	0,8 1,8	– 0,5	– –	0,2 0,8	0,2 0,8	– 0,5	Rem. –	– 0,3	8,2
CuZn40Mn2Fe1	CW723R	min. max.	56,5 58,5	– 0,1	– –	0,5 1,5	1,0 2,0	– 0,6	– –	– 0,5	– 0,1	– 0,3	Rem. –	– 0,4	8,3
†† For information only.															
‡‡ See note to clause 1.															

Table 9: Mechanical properties of copper and low alloyed copper alloys

Designations		Material condition	Wall thickness t mm	Tensile strength R_m N/mm ²	0,2% proof strength		Elongation	Hardness				
Symbol	Number				$R_{p0,2}$ N/mm ²			A %	HV		HB	
					min.	max.			min.	max.	min.	max.
Cu-DHP	CW024A	M	20	—	—	—	—	—	—	—	—	—
		R200 ¹⁾	20	200	—	110	40	—	—	—	—	
		H040 ¹⁾	20	—	—	—	—	40	65	35	60	
		R250	10	250	150	—	20	—	—	—	—	
		H070	10	—	—	—	—	70	100	65	95	
		R290	5	290	250	—	5	—	—	—	—	
		H095	5	—	—	—	—	95	120	90	115	
		R360	3	360	320	—	—	—	—	—	—	
		H110	3	—	—	—	—	110	—	105	—	
		M	20	—	—	—	—	—	—	—	—	
CuFe2P	CW107C	R300 ¹⁾	10	300	—	250	25	—	—	—	—	
		H085 ¹⁾	10	—	—	—	—	85	115	80	110	
		R370	5	370	250	—	15	—	—	—	—	
		H110	5	—	—	—	—	110	140	105	135	
		R420	5	420	320	—	5	—	—	—	—	
		H135	5	—	—	—	—	135	—	130	—	

(continued)

(continued)

Table 9 (concluded)

Designations			Wall thickness <i>t</i> mm	Tensile strength <i>R_m</i> N/mm ²	0,2% proof strength		Elongation A %	Hardness					
Symbol	Material	Material condition			Number	<i>R_{p0,2}</i> N/mm ²		min.	max.	HV		HB	
										min.	max.	min.	max.
CuNi2Si	CW111C	M		max. 20	—	—	—	—	—	—	—	—	—
		R260 ²⁾		10	260	60	—	—	30	—	—	—	—
		H065 ²⁾		10	—	—	—	—	—	65	100	60	90
		R460 ³⁾		10	460	300	—	—	12	—	—	—	—
		H150 ³⁾		10	—	—	—	—	—	150	190	140	180
		R380 ⁴⁾		10	380	260	—	—	6	—	—	—	—
		H130 ⁴⁾		10	—	—	—	—	—	130	170	120	160
		R600 ⁵⁾		10	600	480	—	—	8	—	—	—	—
H190 ⁵⁾		10	—	—	—	—	—	190	—	180	—		
¹⁾ Annealed condition.													
²⁾ Solution heat treated.													
³⁾ Solution heat treated and precipitation hardened.													
⁴⁾ Solution heat treated and cold formed.													
⁵⁾ Solution heat treated, cold formed and precipitation hardened.													
NOTE: 1 N/mm ² is equivalent to 1 MPa.													

Table 10: Mechanical properties of copper-nickel alloys

Designations		Material		Wall thickness	Tensile strength	0,2% proof strength	Elongation	Hardness			
Symbol	Number	Material condition	t	R_m	$R_{p0,2}$	A	HV	HB			
			mm	N/mm ²	N/mm ²	%					
		M	max.	min.	min.	min.	min.	max.	min.	max.	
			20	—	—	—	—	—	—	—	
CuNi10Fe1Mn	CW352H	R290 ¹⁾	20	290	90	30	—	—	—	—	
		H075 ¹⁾	20	—	—	—	75	110	70	105	
		R310	6	310	220	12	—	—	—	—	
		H105	6	—	—	—	105	—	100	—	
		R480	4	480	400	8	—	—	—	—	
		H150	4	—	—	—	150	—	145	—	
CuNi30Mn1Fe	CW354H	M	20	—	—	—	—	—	—	—	
		R370 ¹⁾	10	370	120	35	—	—	—	—	
		H085 ¹⁾	10	—	—	—	85	120	80	115	
		R480	5	480	300	12	—	—	—	—	
		H135	5	—	—	—	135	—	130	—	
		¹⁾ Annealed condition.									

NOTE: 1 N/mm² is equivalent to 1 MPa.

Table 11: Mechanical properties of copper-nickel-zinc alloys

Designations		Material condition		Wall thickness	Tensile strength	0,2% proof strength		Elongation	Hardness		
Symbol	Number	Material	Condition	t	R_m	$R_{p0.2}$		A	HV		HB
				mm	N/mm ²	min.	max.	N/mm ²	min.	max.	min.
CuNi12Zn24	CW403J	M		20	—	—	—	—	—	—	—
		R340 ¹⁾		10	340	—	290	45	—	—	—
		H075 ¹⁾		10	—	—	—	—	75	110	105
		R420		5	420	240	—	25	—	—	—
		H110		5	—	—	—	—	110	140	135
CuNi18Zn20	CW409J	R490		3	490	390	—	10	—	—	—
		H135		3	—	—	—	—	135	—	—
		M		20	—	—	—	—	—	—	—
		R370 ¹⁾		10	370	—	290	40	—	—	—
CuNi18Zn20	CW409J	H080 ¹⁾		10	—	—	—	—	80	115	110
		R440		5	440	290	—	20	—	—	—
		H115		5	—	—	—	—	115	150	145
		R540		3	540	450	—	5	—	—	—

NOTE: 1 N/mm² is equivalent to 1 MPa.

Table 12: Mechanical properties of copper-tin alloys

Designations			Wall thickness <i>t</i> mm	Tensile strength <i>R_m</i> N/mm ²	0,2% proof strength		Elongation A %	Hardness				
Material	Material condition	Symbol			Number	<i>R_{p0,2}</i> N/mm ²		HV		HB		
						min.		max.	min.	max.	min.	max.
CuSn6	CW452K	M	20	—	—	—	—	—	—	—	—	
			10	340	—	260	50	—	—	—	—	
			10	—	—	—	—	70	105	65	100	
			5	400	220	—	30	—	—	—	—	
			5	—	—	—	—	105	150	100	145	
			3	490	390	—	10	—	—	—	—	
			3	—	—	—	—	140	175	135	170	
			2	580	500	—	5	—	—	—	—	
			2	—	—	—	—	170	—	165	—	
			(continued)									

(continued)

Table 12 (continued)

Designations		Wall thickness <i>t</i> mm	Tensile strength <i>R_m</i> N/mm ²	0,2% proof strength <i>R_{p0,2}</i> N/mm ²		Elongation <i>A</i> %	Hardness			
Symbol	Material						HV		HB	
	Material condition	max.	min.	min.	max.	min.	min.	max.	min.	max.
	M	20	—	—	—	—	—	—	—	—
	R380 ⁽¹⁾	10	380	—	290	55	—	—	—	—
	H080 ⁽¹⁾	10	—	—	—	—	80	110	75	105
	R450	5	450	250	—	25	—	—	—	—
	H115	5	—	—	—	—	115	160	110	155
	R520	3	520	440	—	10	—	—	—	—
	H155	3	—	—	—	—	155	190	150	185
	R590	2	590	520	—	5	—	—	—	—
	H180	2	—	—	—	—	180	—	175	—

(continued)

Table 12 (concluded)

Designations		Material condition		Wall thickness <i>t</i> mm	Tensile strength <i>R_m</i> N/mm ²	0,2% proof strength <i>R_{p0,2}</i> N/mm ²		Elongation <i>A</i> %	Hardness			
Symbol	Number			max.	min.	min.	max.	min.	min.	max.	max.	
CuSn4Pb2P	CW455K	M		20	—	—	—	—	—	—	—	
		R430		10	430	220	—	25	—	—	—	—
		H125		10	—	—	—	—	125	155	120	150

Table 13: Mechanical properties of binary copper-zinc alloys

Designations		Material condition	Wall thickness t mm	Tensile strength R_m N/mm ²	0,2% proof strength		Elongation	Hardness				
Symbol	Number				$R_{p0.2}$ N/mm ²			A %	HV		HB	
					min.	max.			min.	max.	min.	max.
CuZn5	CW500L	M	20	—	—	—	—	—	—	—	—	—
		R220 ¹⁾	20	220	—	130	40	—	—	—	—	—
		H050 ¹⁾	20	—	—	—	—	50	75	45	70	
		R260	10	260	190	—	18	—	—	—	—	—
		H075	10	—	—	—	—	75	105	70	100	
		R320	5	320	260	—	8	—	—	—	—	—
		H095	5	—	—	—	—	95	125	90	120	
		R440	3	440	410	—	—	—	—	—	—	—
		H120	3	—	—	—	—	120	—	115	—	—
		M	20	—	—	—	—	—	—	—	—	—
		R240 ¹⁾	20	240	—	140	40	—	—	—	—	—
		H050 ¹⁾	20	—	—	—	—	50	80	45	75	
CuZn10	CW501L	R300	10	300	180	—	20	—	—	—	—	—
		H075	10	—	—	—	—	75	105	70	100	
		R360	5	360	280	—	8	—	—	—	—	—
		H100	5	—	—	—	—	100	—	95	—	—

(continued)

(continued)

Table 13: (continued)

Designations		Material condition	Wall thickness	Tensile strength	0,2% proof strength		Elongation	Hardness			
Symbol	Number		t mm	R_m N/mm ²	$R_{p0.2}$ N/mm ²		A %	HV		HB	
					min.	max.		min.	max.	min.	max.
CuZn15	CW502L	M	20	—	—	—	—	—	—	—	—
		R260 ¹⁾	20	260	—	150	42	—	—	—	—
		H050 ¹⁾	20	—	—	—	—	50	80	45	75
		R310	10	310	200	—	20	—	—	—	—
		H080	10	—	—	—	—	80	110	75	105
		R370	5	370	290	—	10	—	—	—	—
		H105	5	—	—	—	—	105	—	100	—
		M	20	—	—	—	—	—	—	—	—
		R260 ¹⁾	20	260	—	160	45	—	—	—	—
		H055 ¹⁾	20	—	—	—	—	55	85	50	80
CuZn20	CW503L	R320	10	320	200	—	25	—	—	—	—
		H085	10	—	—	—	—	85	120	80	115
		R390	5	390	300	—	10	—	—	—	—
		H115	5	—	—	—	—	115	—	110	—
		(continued)									

Table 13: (continued)

Designations		Material condition	Wall thickness <i>t</i> mm	Tensile strength <i>R_m</i> N/mm ²	0,2% proof strength		Elongation <i>A</i> %	Hardness			
Symbol	Number				min.	max.		HV		HB	
		M	max. 20	min.	—	—	min.	min.	max.	min.	max.
CuZn30	CW505L		20	280	—	180	50	—	—	—	—
		R280 ¹⁾	20	—	—	—	—	—	—	—	—
		H055 ¹⁾	20	—	—	—	—	55	85	50	80
			10	350	200	—	25	—	—	—	—
		R350	10	—	—	—	—	85	120	80	115
		H085	10	—	—	—	—	—	—	—	—
			5	420	320	—	10	—	—	—	—
		H115	5	—	—	—	—	115	—	110	—
CuZn36	CW507L	M	20	—	—	—	—	—	—	—	—
			20	290	—	180	50	—	—	—	—
		R290 ¹⁾	20	—	—	—	—	55	85	50	80
		H055 ¹⁾	20	—	—	—	—	—	—	—	—
			10	360	180	—	25	—	—	—	—
		R360	10	—	—	—	—	80	115	75	110
		H080	10	—	—	—	—	—	—	—	—
			5	430	300	—	12	—	—	—	—
		H110	5	—	—	—	—	110	—	105	—

(continued)

Table 13: (concluded)

Designations			Material		Wall thickness	Tensile strength	0,2% proof strength		Elongation	Hardness				
Symbol	Number	Material condition	t	R_m	$R_{p0,2}$		A	HV	HB	min.	max.	min.	max.	
			mm	N/mm ²	N/mm ²	%								
CuZn37	CW508L	M	20	—	—	—	—	—	—	—	—	—	—	
		R300 ¹⁾	20	300	—	220	45	—	—	—	—	—	—	
		H060 ¹⁾	20	—	—	—	—	60	90	55	85	—	—	
		R370	10	370	200	—	25	—	—	—	—	—	—	
		H085	10	—	—	—	—	85	120	80	115	—	—	
		R440	5	440	320	—	10	—	—	—	—	—	—	
		H115	5	—	—	—	—	115	—	110	—	—	—	
		M	20	—	—	—	—	—	—	—	—	—	—	
		R340 ¹⁾	20	340	—	250	35	—	—	—	—	—	—	
		H075 ¹⁾	20	—	—	—	—	75	105	70	100	—	—	
CuZn40	CW509L	R410	10	410	250	—	18	—	—	—	—	—	—	
		H100	10	—	—	—	—	100	130	95	125	—	—	
		R470	5	470	400	—	5	—	—	—	—	—	—	
		H125	5	—	—	—	—	125	—	120	—	—	—	
		1) Annealed condition.												
		NOTE: 1 N/mm ² is equivalent to 1 MPa.												

Table 14: Mechanical properties of copper-zinc-lead alloys

Designations		Material		Wall thickness	Tensile strength	0,2% proof strength		Elongation	Hardness			
Symbol	Number		Material condition	t mm	R_m N/mm ²	$R_{p0,2}$ N/mm ²		A %	HV		HB	
				max.	min.	min.	max.	min.	min.	max.	min.	max.
			M	20	—	—	—	—	—	—	—	—
CuZn35Pb1 CuZn35Pb2 ²⁾	CW600N CW601N ²⁾		R290 ¹⁾	10	290	—	180	45	—	—	—	—
			H060 ¹⁾	10	—	—	—	—	60	90	55	85
			R370	10	370	200	—	20	—	—	—	—
			H085	10	—	—	—	—	85	120	80	115
			R440	5	440	340	—	10	—	—	—	—
			H115	5	—	—	—	—	115	—	110	—
CuZn36Pb2As ²⁾	CW602N ²⁾		M	20	—	—	—	—	—	—	—	—
			R290 ¹⁾	10	290	—	250	40	—	—	—	—
			H080 ¹⁾	10	—	—	—	—	80	110	75	105
			R370	10	370	250	—	20	—	—	—	—
			H105	10	—	—	—	—	105	140	100	135
			R440	5	440	340	—	10	—	—	—	—
			H135	5	—	—	—	—	135	—	130	—

(continued)

Table 14 (continued)

Designations		Material condition	Wall thickness <i>t</i> mm	Tensile strength <i>R_m</i> N/mm ²	0,2% proof strength		Elongation <i>A</i> %	Hardness			
Symbol	Number				min.	max.		HV		HB	
			max.	min.	min.	max.	min.	min.	max.	min.	max.
CuZn36Pb3 ²⁾	CW603N ²⁾	M	20	—	—	—	—	—	—	—	—
		R300 ¹⁾	10	300	—	250	35	—	—	—	—
		H080 ¹⁾	10	—	—	—	—	80	110	75	105
		R400	10	400	250	—	15	—	—	—	—
		H105	10	—	—	—	—	105	140	100	135
		R460	5	460	350	—	10	—	—	—	—
		H135	5	—	—	—	—	135	—	130	—
		M	20	—	—	—	—	—	—	—	—
		R300 ¹⁾	20	300	—	220	45	—	—	—	—
		H060 ¹⁾	20	—	—	—	—	60	90	55	85
CuZn37Pb0,5 CuZn37Pb1 ²⁾	CW604N CW605N ²⁾	R370	10	370	200	—	25	—	—	—	—
		H085	10	—	—	—	—	85	120	80	115
		R440	5	440	320	—	10	—	—	—	—
		H115	5	—	—	—	—	115	—	110	—

(continued)

Table 14 (concluded)

Designations			Material condition	Wall thickness <i>t</i> mm	Tensile strength <i>R_m</i> N/mm ²	0,2% proof strength		Elongation <i>A</i> %	Hardness					
Symbol	Number	Material				<i>R_{p0.2}</i> N/mm ²	min.		max.	HV		HB		
										min.	max.	min.	max.	
CuZn38Pb1 ²⁾ CuZn38Pb2 ²⁾	CW607N ²⁾ CW608N ²⁾	M	20	—	—	—	—	—	—	—	—	—	—	—
		R340 ¹⁾	10	340	—	250	35	—	—	—	—	—	—	—
		H080 ¹⁾	10	—	—	—	—	80	110	140	100	135	—	—
		R410	10	410	250	—	15	—	—	—	—	—	—	—
		H105	10	—	—	—	—	105	140	100	135	—	—	
		R470	5	470	350	—	10	—	—	—	—	—	—	—
CuZn39Pb3 ²⁾ CuZn40Pb2 ²⁾	CW614N ²⁾ CW617N ²⁾	H135	5	—	—	—	—	—	135	—	—	130	—	—
		M	20	—	—	—	—	—	—	—	—	—	—	—
		R360 ¹⁾	10	360	—	250	25	—	—	—	—	—	—	—
		H085 ¹⁾	10	—	—	—	—	85	120	80	115	—	—	
		R430	10	430	250	—	12	—	—	—	—	—	—	—
		H115	10	—	—	—	—	115	150	110	145	—	—	
Annealed condition.		R500	5	500	370	—	8	—	—	—	—	—	—	—
		H140	5	—	—	—	—	140	—	—	135	—	—	—

¹⁾ Annealed condition.
²⁾ See note to clause 1.
NOTE: 1 N/mm² is equivalent to 1 MPa.

¹⁾ Annealed condition.

²⁾ See note to clause 1.

NOTE: 1 N/mm² is equivalent to 1 MPa.

Table 15: Mechanical properties of complex copper-zinc alloys

Designations		Material		Wall thickness	Tensile strength	0,2% proof strength	Elongation	Hardness			
Symbol	Number	Material condition	t mm	R_m N/mm ²	$R_{p0,2}$ N/mm ²	A %	min.	min.	max.	min.	max.
CuZn13Al1Ni1Si1	CW700R	M	20	—	—	—	—	—	—	—	—
		R380 ⁽¹⁾	10	380	115	50	—	—	—	—	—
		H065 ⁽¹⁾	10	—	—	—	65	65	85	60	80
		R430	10	430	220	40	—	—	—	—	—
		H120	10	—	—	—	120	120	140	115	135
		R550	5	550	330	10	—	—	—	—	—
CuZn20Al2As	CW702R	H170	5	—	—	—	170	170	—	165	—
		M	20	—	—	—	—	—	—	—	—
		R340 ⁽¹⁾	10	340	120	45	—	—	—	—	—
		H070 ⁽¹⁾	10	—	—	—	70	70	100	65	95
		R390 ⁽¹⁾	5	390	150	40	—	—	—	—	—
		H085 ⁽¹⁾	5	—	—	—	85	85	—	80	—

(continued)

Table 15 (continued)

Designations		Wall thickness <i>t</i> mm	Tensile strength <i>R_m</i> N/mm ²	0,2% proof strength <i>R_{p0,2}</i> N/mm ²	Elongation <i>A</i> %	Hardness			
Symbol	Number					HV		HB	
Material	Material condition	max.	min.	min.	min.	min.	max.	min.	max.
CuZn31Si1	CW708R	M	—	—	—	—	—	—	—
		R440	440	200	20	—	—	—	—
		H115	—	—	—	115	155	110	150
		R490	490	250	15	—	—	—	—
		H145	—	—	—	145	—	140	—
		M	—	—	—	—	—	—	—
		R490	490	290	15	—	—	—	—
		H125	—	—	—	125	165	120	160
		R540	540	390	10	—	—	—	—
		H145	—	—	—	145	—	140	—
		M	—	—	—	—	—	—	—
		R540	540	250	10	—	—	—	—
CuZn37Mn3Al2PbSi ²⁾	CW713R ²⁾	H145	—	—	—	145	185	140	180
		R590	590	320	8	—	—	—	—
		H155	—	—	—	155	195	150	190
		R640	640	350	5	—	—	—	—
		H165	—	—	—	165	—	160	—

(continued)

Table 15 (concluded)

Designations		Material condition	Wall thickness	Tensile strength	0.2% proof strength	Elongation	Hardness				
Symbol	Number		t	R_m	$R_{p0.2}$	A	HV		HB		
			mm	N/mm ²	N/mm ²	%	min.	max.	min.	max.	
CuZn38Mn1Al	CW716R	M	20	—	—	—	—	—	—	—	—
		R440	8	440	200	15	—	—	—	—	—
		H115	8	—	—	—	115	155	110	150	
CuZn39Mn1AlPbSi	CW718R	R510	8	510	270	10	—	—	—	—	—
		H140	8	—	—	—	140	—	135	—	—
		M	20	—	—	—	—	—	—	—	—
CuZn40Mn2Fe1	CW723R	R440	8	440	200	15	—	—	—	—	—
		H120	8	—	—	—	120	160	115	155	—
		R510	8	510	270	10	—	—	—	—	—
		H145	8	—	—	—	145	—	140	—	—
CuZn40Mn2Fe1	CW723R	M	20	—	—	—	—	—	—	—	—
		R440	8	440	170	15	—	—	—	—	—
		H115	8	—	—	—	115	155	110	150	—
CuZn40Mn2Fe1	CW723R	R490	8	490	270	10	—	—	—	—	—
		H135	8	—	—	—	135	—	130	—	—

¹⁾ Annealed condition.

²⁾ See note to clause 1.

NOTE: 1 N/mm² is equivalent to 1 MPa.

Table 16: Tolerances on diameter

Values in millimetres

Nominal diameter		Tolerances on nominal diameter	
over	up to and including	applicable to mean diameter	applicable to any diameter including deviation from circular form for straight lengths ^{1) 2)}
3 ³⁾	10	± 0,06	± 0,12
10	20	± 0,08	± 0,16
20	30	± 0,12	± 0,24
30	50	± 0,15	± 0,30
50	100	± 0,20	± 0,50
100	200	± 0,50	± 1,0
200	300	± 0,75	± 1,5
300	450	± 1,0	± 2,0
¹⁾ The tolerances in this column are not applicable to: - tubes in coiled form (for tolerances on coils see table 20); - tubes with OD/t > 50; - tubes in annealed condition. ²⁾ When the diameter is measured at a distance from the ends of the tube of up to 100 mm or the equivalent of one nominal outside diameter (whichever is the smaller), unless otherwise agreed, the tolerance may be increased by a factor of 3. ³⁾ Including 3.			

Table 17: Tolerances on wall thickness

Nominal outside diameter mm		Tolerances on nominal wall thickness <i>t</i>				
		%				
over	up to and including	<i>t</i> from 0,3 mm up to and including 1 mm	<i>t</i> over 1 mm up to and including 3 mm	<i>t</i> over 3 mm up to and including 6 mm	<i>t</i> over 6 mm up to and including 10 mm	<i>t</i> over 10 mm
3 ¹⁾	40	± 15	± 13	± 11	± 10	—
40	120	± 15	± 13	± 12	± 11	± 10
120	250	—	± 13	± 13	± 12	± 11
250	450	—	—	± 15	± 15	± 15
¹⁾ Including 3.						

Table 18: Tolerances on fixed lengths, tubes in straight lengths

Values in millimetres

Nominal outside diameter		Tolerance on fixed length			
over	up to and including	up to and including 250	over 250 up to and including 1 000	over 1 000 up to and including 4 000	over 4 000
3 ¹⁾	25	+1 0	+3 0	+5 0	by agreement
25	100	+2 0	+5 0	+7 0	
100	450	+3 0	+5 0	+10 0	
1) Including 3.					

Table 19: Tolerances on fixed lengths, tube in coils (not level wound)

Specified length m	Tolerance %
up to and including 50	+2 0
over 50 up to and including 100	+3 0
over 100	+5 0

Table 20: Tolerances on diameter including deviation from circular form, tube in coils

Values in millimetres

Nominal outside diameter		Tolerance on nominal diameter including deviation from circular form	Applicable for coil inside diameter
over	up to and including		min.
3 ¹⁾	6	± 0,30	400
6	10	± 0,50	600
10	20	± 0,70	800
20	30	± 0,90	1 000
¹⁾ Including 3.			

Table 21: Tolerances on straightness

Ratio of		Depth of arc ¹⁾ mm	
over	up to and including	h_1 in any length l_1 of 1 000 mm max.	h_2 in any length l_2 of 400 mm max.
—	5	2	0,8
5	10	3	1,2
10	20	4	1,6
20	40	5	2,0
40	—	6	2,5

¹⁾ See figure 1.

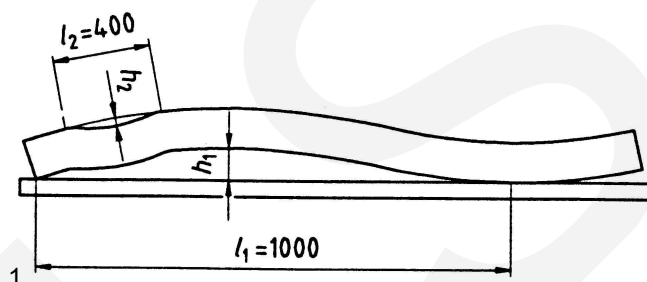


Figure 1: Measurement

of straightness

Table 22: Sampling rate

Mass per unit length kg/m		Size of inspection lot for one test sample kg up to and including
up to and including	0,25	500
over up to and including	0,25 5	1 000
over	5	2 500

NOTE: Larger inspection lots require sampling in proportion, up to a maximum of five test samples.

Annex A (informative)

Bibliography

In the preparation of this European Standard, use was made of a number of documents for reference purposes. These informative references are cited at the appropriate places in the text and the publications are listed hereafter.

EN 1173

Copper and copper alloys – Material condition or temper designation

EN 1412

Copper and copper alloys – European numbering system

EN 12168

Copper and copper alloys – Hollow rod for free machining purposes

EN ISO 9001

Quality systems – Model for quality assurance in design/development, production, installation and servicing (ISO 9001 : 1994)

EN ISO 9002

Quality systems – Model for quality assurance in production, installation and servicing (ISO 9002 : 1994)

ISO 31-0 : 1992

Quantities and units – Part 0: General principles

ISO 1190-1

Copper and copper alloys – Code of designation – Part 1: Designation of materials

ISO 1811-2

Copper and copper alloys – Selection and preparation of samples for chemical analysis – Part 2: Sampling of wrought products and castings

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.